

Zbornik radova Proceedings

**8. Međunarodna konferencija
o obnovljivim izvorima električne energije**
Beograd, 16. oktobar 2020

**8th International Conference
on Renewable Electrical Power Sources**
Belgrade, October 16, 2020

ZBORNİK RADOVA Proceedings

**pisanih za 8. Međunarodnu konferenciju o
obnovljivim izvorima električne energije**

**8th International Conference on Renewable
Electrical Power Sources**

CIP - Katalogizacija u publikaciji - Narodna biblioteka Srbije, Beograd

502.171:620.9(082)(0.034.2)

MEĐUNARODNA konferencija o obnovljivim izvorima električne energije (8 ; 2020 ; Beograd)

Zbornik radova [Elektronski izvor] / 8. Međunarodna konferencija o obnovljivim izvorima električne energije, Beograd, 16. oktobar 2020 ; [urednik Zoran Stević] = Proceedings / 8th International Conference on Renewable Electrical Power Sources, Belgrade, October 16, 2020 ; [editor Zoran Stević]. - Beograd : Savez mašinskih i elektrotehničkih inženjera i tehničara Srbije - SMEITS, 2020 (Beograd : Paragon). - 1 elektronski optički disk (CD-ROM) ; 12 cm

Sistemska zahteva: Nisu navedeni. - Nasl. sa naslovne strane dokumenta. - Tiraž 150. - Abstrakti. - Bibliografija uz svaki rad.

ISBN 978-86-85535-06-2

a) Энергетски извори - Одрживи развој - Зборници

COBISS.SR-ID 25077513



**ZBORNİK RADOVA
pisanih za 8. Međunarodnu konferenciju o
obnovljivim izvorima
električne energije**

Hotel „Zepter“, Beograd
16. oktobar 2020.

**PROCEEDINGS
8th International Conference
on Renewable Electrical
Power Sources**

Hotel „Zepter“, Belgrade
October 16, 2020

Izdavač

Savez mašinskih i
elektrotehničk ihinženjera
i tehničara Srbije (SMEITS)
Društvo za obnovljive izvore
električne energije
Kneza Miloša 7a/II,
11000 Beograd

Publisher

Union of Mechanical and
Electrotechnical Engineers and Technicians of
Serbia (SMEITS)
Society for Renewable Electrical
Power Sources
Kneza Miloša str. 7a/II,
11000 Beograd

**Predsednik Društva za
obnovljive izvore
električne energije
pri SMEITS-u**

Dr Zoran Nikolić, dipl. inž.

**President to the Society
for Renewable Electrical
Power Sources
within the SMEITS**

Zoran Nikolić, Ph. D.

Urednik

Prof. dr Zoran Stević

Editor

Prof Zoran Stević, Ph. D.

Za izdavača

Vladan Galebović

For Publisher

Vladan Galebović

Tiraž

150 primeraka

CD umnožava

Paragon, Beograd

ISBN

978-86-85535-06-2

**Organizator
Organizer**

Savez mašinskih i elektrotehničkih
inženjera i tehničara Srbije (SMEITS),
**Društvo za obnovljive izvore
električne energije**

Union of Mechanical and Electrotechnical
Engineers and Technicians of Serbia (SMEITS),
**Society for Renewable Electrical
Power Sources**

Kneza Miloša 7a/II, 11000 Beograd
Tel. +381 (0) 11 3230-041, +381 (0) 11 3031-696, tel./faks +381 (0) 11 3231-372
office@smeits.rs • www.smeits.rs

Održavanje 8. MKOIEE finansijski je pomoglo
Ministarstvo prosvete, nauke i tehnološkog
razvoja Republike Srbije



Međunarodni programski odbor
International Programme Committee

Prof. dr Slađana Alagić	Srbija
Prof. Viorel Badescu	Rumunija
Prof. dr Pellumb Berberi	Albanija
Prof. dr Miroslav Bjekić	Srbija
Prof. dr Oleksandr Bondarenko	Ukrajina
Prof. dr Alla Denysova	Bugarska
Dr Stevan Dimitrijević	Srbija
Akademik prof. dr Zoran Đurić	Srbija
Dr Aleksandar Ivančić	Španija
Prof. dr Miroljub Jevtić	Srbija
Prof. dr Branko Kovačević	Srbija
Prof. Vladimir Krstić	Kanada
Prof. Nikolay Lopatkin	Rusija
Prof. Nikolay Mihailov	Bugarska
Prof. dr Milica Naumović	Srbija
Prof. dr Stefka Nedeltcheva	Bugarska
Dr Dušan Nikolić	Australija
Dr Zoran Nikolić	Srbija
Prof. dr Elena Ponomaryova	Ukrajina
Dr Mila Pucar	Srbija
Prof. dr Nikola Rajaković	Srbija
Prof. dr Birgit Scheppat	Nemačka
Prof. dr Valerij Sytnikov	Ukrajina
Prof. dr Velimir Stefanović	Srbija
Prof. dr Zoran Stević	Serbia (predsednik)
Prof. dr Zoran Stojiljković	Srbija
Prof. dr Volodymyr Sydorets	Ukrajina
Prof. dr Nada Štrbac	Srbija
Prof. dr Dragan Tasić	Srbija
Prof. dr Michael Todorov	Bugarska
Dr Nataša Tomić	Srbija
Dr Milica Vlahović	Srbija
Dr Zhongying Wang	Kina
Dr Wanxing Wang	Kina
Dr Xuejun Wang	Kina
Prof. dr Hengzhao Yang	SAD
Dr Ruiying Zhang	Kina

Organizacioni odbor
Organizing Committee

Mila Pucar
Rastislav Kragić
Zoran Nikolić (*predsednik*)
Ilija Radovanović
Žarko Ševaljević
Jelena Salević
Vladan Galebović

FOREWORD

Science, technology and industry accelerated development leads to improvements of human life, but also creates new risky situations. Humanity faces unprecedented risks. Global warming is an example. Although most experts in the field of climate change state that global warming is created by humans, some scientists do not agree. One of the main problems in these risky situations is – question of responsibility. The world governments should not leave all responsibility to scientists and experts. Authorities should consult experts to declare state of emergency. A strong political initiative is necessary to start dealing with serious ecological problems such as global warming or local environment pollution. Highest level political agreements achieved within the Kyoto Protocol are not enough to stop these phenomena. Clean technologies designed to provide superior performances at lower prices, with lowering losses of conventional offerings – have great chances to be the next driving force to ensure economy growth.

Science is the first to define problems of Earth and life survival. Science is trying to provide solutions, limited by political, social, economic and technology factors. Preservation of life on Earth is the common priority.

Science and technical and technology development can contribute in several fields:

- renewable power sources;*
- efficient energy usage;*
- waste reducing;*
- harmfulness of waste mitigation;*
- recycling;*
- soil, water and air purification;*
- residual waste neutralization.*

Important factor for political decisions making is the public opinion. Therefore, it is extremely important to raise awareness and widely educate population on necessary transition to renewable, ecologically acceptable power sources, which is one of long-term goals of this Conference.

For eight time, this international event is organized by the Society of Renewable Electrical Power Sources (DOIEE) within the Union of Mechanical and Electrotechnical Engineers and Technicians of Serbia (SMETS).

*Belgrade,
October 2020.*

PREDGOVOR

Ubrzani napredak nauke, tehnologije i industrije dovodi do poboljšanja kvaliteta ljudskog života, ali i do stvaranja novih rizičnih situacija. Čovečanstvo je suočeno sa rizicima kakvih u ranijoj ljudskoj istoriji nije bilo. Globalno zagrevanje je tipičan primer. Iako većina eksperata koji proučavaju klimatske promene tvrde da globalno zagrevanje postoji i da je čovek taj koji ga uzrokuje, postoje naučnici koji dovode u sumnju takve tvrdnje. Jedan od glavnih problema vezanih za nove rizične situacije jeste – pitanje odgovornosti. Vlade država u svetu ne smeju teret odgovornosti prepustiti isključivo naučnicima i ekspertima. Vlasti treba da se konsultuju sa ekspertima i da dobro procene kada treba proglasiti opasnost od rizične situacije. Potrebna je jaka politička inicijativa da bi se počeli rešavati ozbiljni ekološki problemi kao što je globalno zagrevanje, ali i lokalno zagađenje životne sredine. Politički dogovori na svetskom nivou koji su do sada postignuti u okviru Kjoto protokola, nedovoljni su za zaustavljanje ovog fenomena. Čiste tehnologije – tehnologije koje su dizajnirane da obezbeđuju superiorne performanse za nižu cenu dok istovremeno kreiraju manji gubitak od konvencionalnih ponuda – imaju velike šanse da budu sledeća motorna snaga koja će obezbediti ekonomski rast.

Nauka, naravno, pre svih uočava probleme opstanka planete i života na njoj. Ona takođe pokušava da ih reši i uspeva onoliko koliko je to realno moguće, imajući u vidu političke, socijalne, ekonomske i tehnološke faktore. Može se konstatovati da su praktično svi prioriteti posvećeni očuvanju života na Zemlji. Nauka i razvoj tehnike i tehnologije mogu tome doprineti u više segmenata:

- obnovljivi izvori energije;*
- energetska efikasnost;*
- smanjenje količine otpada;*
- smanjenje štetnosti otpada;*
- reciklaža;*
- prečišćavanje zemlje, vode i vazduha;*
- neutralizacija preostalog otpada.*

Bitan faktor za donošenje političkih odluka je i javno mnjenje. Zato je jako važno podizanje opšte svesti i što šira edukacija stanovništva o neophodnosti prelaska na obnovljive, ekološki prihvatljive izvore energije, što je jedan od dugoročnih ciljeva ove Konferencije.

Ovaj međunarodni skup po osmi put organizuje Društvo za obnovljive izvore električne energije (DOIEE) Saveza mašinskih i elektrotehničkih inženjera i tehničara Srbije (SMEITS).

*U Beogradu,
oktobra 2020.*

SADRŽAJ / CONTENTS

PREDGOVOR

Prof. dr Zoran STEVIĆ 7

1. Novi materijali i nove tehnologije u oblasti OIE

Plenarno predavanje – po pozivu

1. “SUPERALKALNI“ KLASTERI, PROIZVODNJA,
POTENCIJALNA PRIMENA KAO MATERIJAL
ZA SKLADIŠTENJE ENERGIJE
“SUPERALKALI” CLUSTERS, PRODUCTION, POTENTIAL
APPLICATION LIKE ENERGY STORAGE MATERIALS
Suzana VELIČKOVIĆ, Xianglei KONG 15

Redovna izlaganja

2. UPOTREBA NIKLA KAO MEĐUPREVLAKE U CILJU SMANJENJA
KONTAKTNE KOROZIJE NA ELEKTRIČNIM KONTAKTIMA AL-CU
USE OF NICKEL AS AN INTERMEDIATE COATING TO REDUCE
CONTACT CORROSION ON ELECTRICAL CONTACTS AL-CU
Silvana DIMITRIJEVIĆ, Zoran STEVIĆ, Aleksandra IVANOVIĆ,
Stevan DIMITRIJEVIĆ, Saša MARJANOVIĆ, Nikhil DHAWAN 23
3. SINTEZA SREBRNIH ČESTICA VELIČINE MIKROMETRA
PRIMENJIVE ZA DEBELO FILMNE KONTAKTE
NA SOLARNIM ČELIJAMA
SYNTHESIS OF MICRO-SIZED SILVER PARTICLES SUITABLE
FOR THICK FILM CONTACTS ON SOLAR CELLS
Stevan DIMITRIJEVIĆ, Silvana DIMITRIJEVIĆ,
Michele MILICIANI, Željko KAMBEROVIĆ,
Zara CHERKEZOVA-ZHELEVA. 29
4. SINTEZA I KARAKTERIZACIJA PREMAZA EPOKSIDNE SMOLE
SA POBOLJŠANOM OTPORNOŠĆU NA PLAMEN UPOTREBOM
MODIFIKOVANE TANINSKE KISELINE
SYNTHESIS AND CHARACTERIZATION OF EPOXY RESIN COATING
WITH IMPROVED FIRE RESISTANCE BY THE ADDITION
OF MODIFIED TANNIC ACID
Andreja ŽIVKOVIĆ, Nataša TOMIĆ,
Marija VUKSANOVIĆ, Aleksandar MARINKOVIĆ 35
5. PRIMENA KONCEPTA 3D ŠTAMPE BETONA
U IZRADI VETROGENERATORA
APPLYING CONCEPT OF 3D PRINTING CONCRETE
IN WIND TOWER CONSTRUCTION
Aleksandar SAVIĆ, Miša STEVIĆ, Sanja MARTINOVIĆ,
Milica VLAHOVIĆ, Tatjana VOLKOV HUSOVIĆ 43
6. TERMOVIZIJSKI MONITORING TOPLOTE HIDRATACIJE BETONA
THERMOVISION MONITORING OF CONCRETE HEAT OF HYDRATION
Aleksandar SAVIĆ, Zoran STEVIĆ, Sanja MARTINOVIĆ,
Milica VLAHOVIĆ, Tatjana VOLKOV HUSOVIĆ 47

7.	UTICAJ MEHANOHEMIJSKE AKTIVACIJE KOMPONENTI NA SINTEZU KORDIJERITNE KERAMIKE ZA PRIMENU U ELEKTRONICI INFLUENCE OF MECHANOCHEMICAL ACTIVATION OF COMPONENTS ON SYNTHESIS OF CORDIERITE CERAMICS FOR APPLICATION IN ELECTRONICS Nataša ĐORĐEVIĆ, Milica VLAHOVIĆ, Slavica MIHAJLOVIĆ, Sanja MARTINOVIĆ	51
8.	UTICAJ VREMENA RELAKSACIJE AKTIVIRANE SMEŠE NA SINTEZU KERAMIKE ZA NAMENU U ELEKTRONICI IMPACT OF RELAXATION TIME OF ACTIVATED MIXTURE ON CERAMICS SYNTHESIS FOR ELECTRONICS PURPOSES Nataša ĐORĐEVIĆ, Milica VLAHOVIĆ, Slavica MIHAJLOVIĆ, Sanja MARTINOVIĆ	57
2. Energetski izvori i skladištenje energije		
9.	POTENCIJAL POLJOPRIVREDNE BIOMASE U SISTEMIMA PROIZVODNJE BIOGASA U REPUBLICI SRBIJI POTENTIAL OF AGRICULTURAL BIOMASS IN BIOGAS PRODUCTION SYSTEMS IN THE REPUBLIC OF SERBIA Olivera EĆIM-ĐURIĆ, Dragan KRECULJ, Danijela ŽIVOJINOVIĆ, Miloš VORKAPIĆ	63
10.	GASIFIKACIJA OSTATAKA BIOMASE ZA POTREBE PROIZVODNJE ELEKTRIČNE ENERGIJE GASIFICATION OF BIOMASS WASTES AND RESIDUES FOR ELECTRICITY PRODUCTION Marta TRNINIĆ	71
11.	POBOLJŠANJE SVOJSTAVA BETONA DODATKOM LETEĆEG PEPELA IZ TERMOELEKTRANE ZA PRIMENU U GEOTERMALNIM SISTEMIMA ENHANCING PROPERTIES OF CONCRETE BY ADDITION OF FLY ASH FROM A THERMAL POWER PLANT FOR APPLICATION IN GEOTHERMAL SYSTEMS Milica VLAHOVIĆ, Aleksandar SAVIĆ, Sanja MARTINOVIĆ, Nataša ĐORĐEVIĆ, Zoran STEVIĆ, Tatjana VOLKOV HUSOVIĆ.	77
12.	PRIMENA OBNOVLJIVIH IZVORA ENERGIJE U ZGRADARSTVU APPLICATION OF RENEWABLE ENERGY RESOURCES IN BUILDINGS Njegoš DRAGOVIĆ, Milovan VUKOVIĆ, Igor UROŠEVIĆ	87
13.	EFIKASNA SINHRONIZACIJA DIZEL GENERATORA U USLOVIMA PROMENLJIVE FREKVENCIJE IMPROVED SYNCHRONIZATION OF DIESEL GENERATORS IN VARIABLE FREQUENCY CONDITIONS USING PREDICTIVE METHOD Zoran NIKOLIĆ, Dušan NIKOLIĆ	95
14.	KORIŠĆENJE OBNOVLJIVIH IZVORA – PRETVARANJE GEOTERMALNE ENERGIJE U ELEKTRIČNU UTILIZING RENEWABLE RESOURCES – CONVERTING GEOTHERMAL ENERGY TO ELECTRICITY Miljan VLAHOVIĆ, Milica VLAHOVIĆ, Zoran STEVIĆ	101
15.	OBNOVLJIVI IZVORI ENERGIJE, POTENCIJALI I PRIMENA U SVETSKIM OKVIRIMA I U SRBIJI RENEWABLE ENERGY SOURCES, POTENTIALS AND APPLICATIONS WORLDWIDE AND IN SERBIA Miomir MIKIĆ, Sanja PETROVIC, Zorica SOVRLIĆ, Daniela UROŠEVIĆ	111

16.	OCENA ŽIVOTNOG CIKLUSA BIOENERGETSKIH SISTEMA LIFE CYCLE ASSESSMENT OF BIOENERGY SYSTEMS Slobodan CVETKOVIĆ, Mirjana KIJEVČANIN.	119
3. Energija vetra		
17.	VETROTURBINE SNAGE PREKO 20 MW – TEHNOLOŠKA PERSPEKTIVA WIND TURBINE BEYOND 20 MW – TECHNOLOGY PERSPECTIVE Aleksandar SIMONOVIĆ, Aleksandar KOVAČEVIĆ, Toni IVANOV, Miloš VORKAPIĆ	123
18.	NUMERIČKA PROCENA AERODINAMIČKIH PERFORMANSI ROTORA VETROTURBINE SA VERTIKALNOM OSOM OBR TANJA I KONCENTRATOROM NUMERICAL EVALUATION OF AERODYNAMIC PERFORMANCES OF VERTICAL-AXIS WIND TURBINE ROTOR WITH FLOW CONCENTRATOR Jelena SVORCAN, Ognjen PEKOVIĆ, TONI IVANOV, Miloš VORKAPIĆ	135
19.	UPRAVLJANJE PRETVARAČIMA U VETROTURBINAMA CONTROL OF CONVERTERS IN WIND TURBINES Stevan JOKIĆ, Zoran STEVIĆ	143
4. Solarna energija		
20.	NAPREDNI SOFTVERSKI SISTEM ZA MONITORING SOLARNOG NAPA JANJA ADVANCED SOFTWARE SYSTEM FOR MONITORING OF SOLAR PANELS Vuk JOVANOVIĆ, Ilija RADOVANOVIĆ, Zoran STEVIĆ.	155
21.	ANALIZA I POREĐENJE RAZLIČITIH METODA MPPT KOD PV SISTEMA NAPA JANJA ANALYSIS AND COMPARISON OF DIFFERENT MPPT METHODS IN PV POWER SYSTEMS Zoran STEVIĆ, Miša STEVIĆ, Ilija RADOVANOVIĆ	159
22.	SOLARNA ENERGIJA U SRBIJI SOLAR ENERGY IN SERBIA 163 Sanja PETROVIĆ, Mimir MIKIĆ, Daniela UROŠEVIĆ	163
23.	MOGUĆNOSTI IMPLEMENTACIJE FOTONAPONSKIH SOLARNIH PANELA U PODRUČJIMA NAMENJENIM VIŠEPORODIČNOM STANOVANJU POSSIBILITIES OF IMPLEMENTATION OF PHOTOVOLTAIC SOLAR PANELS IN MULTI-FAMILY HOUSING AREAS Borjan BRANKOV, Ana STANOJEVIĆ, Mila PUCAR, Marina NENKOVIĆ-RIZNIC	167
24.	PRIMENA SOLARNE ENERGIJE U FUNKCIJI ODRŽIVOG RAZVOJA U JP EPS, OGRANAK RB „KOLUBARA“ - ORG. CEL. PRERADA APPLICATION OF SOLAR ENERGY IN THE FUNCTION OF SUSTAINABLE DEVELOPMENT IN PC EPS, BRANCH OF RB „KOLUBARA“ - ORG. CEL. PROCESSING Momčilo MOMČILOVIĆ, Milisav TOMIĆ.	177

5. Energetska efikasnost

25. **ENERGETSKA EFIKASNOST U SEKTORU JAVNIH ZGRADA NA TERITORIJI GRADA KRAGUJEVCA – STUDIJA SLUČAJA OŠ „MILUTIN I DRAGINJA TODOROVIĆ“**
ENERGY EFFICIENCY IN THE PUBLIC BUILDINGS SECTOR IN THE TERRITORY OF THE CITY OF KRAGUJEVAC – CASE STUDY OF “MILUTIN AND DRAGINJA TODOROVIĆ” ELEMENTARY SCHOOL
Ana RADOJEVIĆ, Aleksandar NEŠOVIĆ,
Jasmina SKERLIĆ, Dušan GORDIĆ, Danijela NIKOLIĆ 189
26. **SIMULACIJA INVERTORA ZA INDUKCIONO GREJANJE**
SIMULATION OF INVERTERS FOR INDUCTION HEATING
Biljana BAKOVIĆ, Zoran STEVIĆ. 199
27. **PRIMENA SUPERKONDENZATORA U ELEKTRIČNIM VOZILIMA**
APPLICATION OF SUPERCAPACITORS IN ELECTRIC VEHICLES
Zoran STEVIĆ, Ilija RADOVANOVIĆ, Miša STEVIĆ 207
28. **ENERGETSKI EFIKASAN SISTEM ZA STERILIZACIJU DRVETA**
ENERGY EFFICIENT SISTEM FOR WOOD STERILIZATION
Miloš MARJANOVIĆ, Miša STEVIĆ, Miloš MILEŠEVIĆ,
Žarko ŠEVALJEVIĆ, Sanja PETRONIĆ, Marta TRNINIĆ, Zoran STEVIĆ. 211

6. Aplikacije i usluge

29. **KOJE VEŠTINE SU POTREBNE U PROIZVODNJI LITIJUM-JONSKIH BATERIJA ZA ELEKTRIČNA VOZILA**
WHAT SKILLS ARE NEEDED IN PRODUCTION OF LITHIUM-ION BATTERIES FOR ELECTRICAL VEHICLES
Zoran KARASTOJKOVIĆ 217
30. **PRIMENA LASERA U AUTOMOBILSKOJ INDUSTRIJI**
APPLICATION OF LASERS IN AUTOMOTIVE INDUSTRY
Milesa SREĆKOVIĆ, Nenad IVANOVIĆ, Stanko OSTOJIĆ,
Aleksander KOVAČEVIĆ, Nada RATKOVIĆ KOVAČEVIĆ,
Zoran KARASTOJKOVIĆ, Sanja JEVTIĆ 223
31. **RASTVARANJE KATODNOG MATERIJALA IZ LIB U SUMPORNOJ KISELINI U PRISUSTVU AZOTA**
DISSOLUTION OF LIBS CATHODE MATERIAL IN SULFURIC ACID IN THE PRESENCE OF NITROGEN
Dragana V. MEDIĆ, Snežana M. MILIĆ, Slađana Č. ALAGIĆ,
Zoran M. STEVIĆ, Boban R. SPALOVIĆ, Maja M. NUJKIĆ, Ivan N. ĐORĐEVIĆ. 241
32. **INTEGRACIJA DISTRIBUIRANIH PV SISTEMA U PAMETNIM SREDINAMA KORISTECI FOG COMPUTING ARHITEKTURU**
INTEGRATION OF DISTRIBUTED PHOTOVOLTAIC SYSTEMS IN THE SMART ENVIRONMENT THROUGH FOG COMPUTING ARCHITECTURE 247
Ilija RADOVANOVIĆ, Ivan POPOVIĆ. 247
33. **PRIMENA METODOLOGIJE PAMETNIH MREŽA U DISTRIBUCIJI ELEKTRIČNE ENERGIJE**
SMART GRID TECHNOLOGY IN POWER DISTRIBUTION SYSTEMS
Ivan POPOVIĆ. 251
34. **MOGUĆNOSTI PRIMENE IIOT PLATFORME U ELEKTROENERGETSKIM SISTEMIMA**
POSSIBILITIES OF IIOT APPLICATION PLATFORMS IN THE ELECTRICAL POWER SYSTEMS 255
Vojkan NIKOLIĆ, Zoran STEVIĆ, Stefana JANIĆIJEVIĆ, Dragan KRECULJ 255

35.	ISTRAŽIVANJE UTICAJA RELATIVNE VLAŽNOSTI I TEMPERATURE NA IOT REŠENJE ZASNOVANO NA JEFTINIM SENZORIMA ZA PRAĆENJE KVALITETA VAZDUHA INVESTIGATION OF THE INFLUENCE OF RELATIVE HUMIDITY AND TEMPERATURE ON THE IOT SOLUTION WITH LOW COST AIR QUALITY MONITORING SENSORS Ivan VAJS, Dejan DRAJIĆ, Ilija RADOVANOVIĆ.	261
36.	RAČUNARSKO UPRAVLJANJE ENERGETSKI EFIKASNIM SISTEMOM ZA STERILIZACIJU DRVETA COMPUTER CONTROL OF ENERGY EFFICIENT WOOD STERILIZATION SYSTEM Miša STEVIĆ, Miloš MARJANOVIĆ, Ilija RADOVANOVIĆ, Zoran STEVIĆ.	267
37.	VAŽNOST PRIMENE ANALIZE RIZIKA KOD OPREME POD PRITISKOM KOJA SE ISPITUJE PO POSEBNOM PROGRAMU IMPORTANCE OF APPLYING RISK ANALYSIS TO PRESSURE EQUIPMENT TESTED BY A SPECIAL PROGRAM Sanja PETRONIĆ, Marko JARIĆ, Katarina ČOLIĆ, Suzana POLIĆ, Dimitrije MALJEVIĆ.	271
38.	AUTOMATIZACIJA PROCESA PROIZVODNJE BAKARNE ŽICE METODOM LIVENJA U VIS – PODSISTEM ZA INDUKCIONO ZAGREVANJE AUTOMATION OF A COPPER WIRE MANUFACTURING PROCESS USING UP-CASTING METHOD – SUBSYSTEM FOR INDUCTION HEATING Nada RATKOVIĆ KOVAČEVIĆ, Misa STEVIĆ, Milos MILEŠEVIĆ, Srđan MAKSIMOVIĆ, Đorđe DIHOVIČNI, Zoran STEVIĆ.	279
39.	POVEĆANJE TOLERANCIJE GREŠKE ADC AD7799 INCREASING FAULT TOLERANCE OF ADC AD7799 Artem BASKO, Elena PONOMARYOVA.	287
40.	MOGUĆNOST KORIŠĆENJA KOŠTICA VIŠNJE KAO BIOGORIVA ZA DOBIJANJE TOPLOTNE ENERGIJE POSSIBILITY OF USING SOUR CHERRY PITS AS BIOFUEL FOR OBTAINING THERMAL ENERGY Milorad PETROVIĆ, Milan JOVANOVIĆ, Zoran ŠTIRBANOVIĆ, Jovica SOKOLOVIĆ, Vojka GARDIĆ.	295

POBOLJŠANJE SVOJSTAVA BETONA DODATKOM LETEĆEG PEPELA IZ TERMoeLEKTRANE ZA PRIMENU U GEOTERMALNIM SISTEMIMA

ENHANCING PROPERTIES OF CONCRETE BY ADDITION OF FLY ASH FROM A THERMAL POWER PLANT FOR APPLICATION IN GEOTHERMAL SYSTEMS

Milica VLAHOVIĆ^{1,1}, Aleksandar SAVIĆ², Sanja MARTINOVIĆ¹, Nataša ĐORĐEVIĆ³,
Zoran STEVIĆ⁴, Tatjana VOLKOV HUSOVIĆ⁵

¹ University of Belgrade, Institute of Chemistry, Technology and Metallurgy, Belgrade, Serbia

² University of Belgrade, Faculty of Civil Engineering, Belgrade, Serbia

³ Institute for Technology of Nuclear and Other Mineral Raw Materials, Belgrade, Serbia

⁴ University of Belgrade, Faculty of Electrical Engineering,
Technical Faculty Bor, CIK Belgrade, Serbia

⁵ University of Belgrade, Faculty of Technology and Metallurgy, Belgrade, Serbia

<https://doi.org/10.24094/mkoiee.020.8.1.77>

Električnu energiju u Srbiji pretežno obezbeđuju termoelektrane. Svih jedanaest termoelektrana u Srbiji koriste uglj, uglavnom lignit u procesu proizvodnje električne energije, čime se godišnje generiše oko 6 miliona tona letećeg pepela. Procenjena količina letećeg pepela iz termoelektrana akumulirana na deponijama u Srbiji prelazi 200 miliona tona. S druge strane, poslednjih decenija poštovanje principa ekološki održivog razvoja nametnuto je industrijama, a jedna od njih je i građevinska. Zahvaljujući prisustvu amorfnog SiO₂ i Al₂O₃, pepeo kao pucolanski materijal pogodan je za proizvodnju betona i maltera. Zbog toga se pravilnom upotrebom letećeg pepela mogu očekivati višestruki pozitivni efekti- smanjenje deponija i poboljšanje svojstava betona. Ideja ovog istraživanja je analiziranje mogućnosti recikliranja letećeg pepela iz termoelektrane tako što će delimično zameniti uobičajeni mineralni punioci- krečnjak u proizvodnji samozbijajućeg betona (SCC). Upoređena su svojstva konvencionalnog SCC sa krečnjakom i kompozicija sa različitim sadržajem pepela. S obzirom da je u slučaju dodatka letećeg pepela potrebno da budu zadovoljeni zahtevi za SCC, kao i da svojstva betona ostanu ista ili poboljšana, ova studija je pokazala da se sve dizajnirane smeše mogu koristiti za konstrukcijske primene.

Ključne reči: samozbijajući beton (SCC); leteći pepeo; dizajn smeša; fizičko-mehanička svojstva; mikrostruktura

Electric power in Serbia is predominantly provided by thermal power plants. All of eleven existing thermal power plants in Serbia use coal, mainly lignite in the electricity production process thus generating about 6 million tons of fly ash per year. The estimated amount of fly ash from thermal power plants accumulated in Serbian landfills exceeds 200 million tons. On the other hand, during the last decades, respecting the principles of ecologically sustainable development has been imposed on industries, and one of them is the construction industry. Due to the presence of amorphous SiO₂ and Al₂O₃, fly ash as pozzolanic material is convenient for the production of concrete and mortar. Consequently, multiple positive effects can be expected by the proper consumption of fly ash- reducing landfills and improving concrete properties. The idea of this study is to analyze the possibility of recycling fly ash from a thermal power plant by replacing a part of common mineral filler- limestone in the production of self-compacting concrete (SCC). Properties of conventional SCC with limestone and compositions with different fly ash content were compared. Considering that requirements for

¹ Corresponding author, email: mvlahovic@tmf.bg.ac.rs

SCC should be satisfied and all properties remain or enhance in the case of fly ash addition, this study proved that all designed concretes can be used for structural applications.

Key words: *self-compacting concrete (SCC); fly ash; mixture design; physico-mechanical properties; microstructure*

1 Introduction

About 70 % of electric power in Serbia is generated in the existing 11 thermal power plants belonging to the Electric Power Industry of Serbia and they all use coal, mostly lignite, thus making them the largest lignite producers. In this electricity production, about 6 million tonnes of fly ash (FA) per year is obtained, which is stored in landfills covering an area around 1,800 ha. The total estimated amount of fly ash in Serbian landfills is over 200 million tonnes [1-3]. Fly ash is a fine, loose material that is being collected in the electro filters of the chimneys in thermal power plants with the particle size usually in the range of 1-150 μm .

The development of concrete additives mainly of polycarboxylate-type, led to spreading application of self-compacting concrete (SCC), considered as a revolutionary discovery in concrete technology. This concrete, owing to its own weight, fills the formwork, thus coats reinforcement bars and fulfills all available space, while achieving the highest compactness, important for hardened state properties and durability [4].

Fly ash, capable of reacting with calcium hydroxide at room temperature, due to the presence of SiO_2 and Al_2O_3 in the amorphous form, can be considered as pozzolanic material and therefore, it has been used for decades as an additive in commercial types of cement and for the production of concrete and mortar. Inhomogeneous composition is one of the disadvantages that reduce its use [5-9].

The use of fine FA particles in concrete leads to the effect of the aggregate fluidity, as well as to an increase in the solid to liquid ratio, at the same water/ cement factor; consequently, the risk of segregation and water extraction on the surface reduces.

Due to the spherical shape and glassy surface of the majority of FA particles, usually finer than the cement particles, the addition of 10 mass. % of FA in relation to the cement mass reduces the water requirement by 3-4 %.

The principles of sustainable development and ecology have been constantly and intensively promoted in all spheres. Hence, the consumption of FA will create multiple positive results, including the reduction of accumulated material at landfills and the improvement of concrete properties [5].

The idea in this study is to investigate the possibility of producing high-performance SCC using FA from Thermal Power Plant "Kolubara A", Serbia, without prior processing, for a partial replacement of mineral filler, limestone. It is presumed that small amounts of FA improve hardened SCC properties without serious deterioration of its fresh state properties. The properties of SCCs with different amounts of FA will be compared and accordingly the optimal composition will be recommended.

2 Experimental

2.1 Mixture design and samples preparation

The initial components used for SCC preparation were aggregate, cement, limestone, fly ash and superplasticizer.

Natural aggregate, from the river Danube, mostly with rounded particles, was used in three fractions: I- fine (0-4 mm), II- coarse (4-8 mm), and III- coarse (8-16 mm). The contents of coarser grains (> 4 mm) in fractions I, II, and III were 1.96 %, 5.81 %, and 0 %, respectively. The contents of fine particles in fractions II and III were 1.84 % and 0.94 %, respectively. In fraction I the contents of fine particles, < 0.063 mm and < 0.09 mm, were 0.59 % and 1.68 %, respectively.

A commercial type I Portland cement (*CEM I 42.5R, Lafarge, Serbia*) was used as a binder. Chemical composition of the cement was: 61.64 % CaO , 21.21 % SiO_2 , 2.22 % MgO , 4.81 % Al_2O_3 , 2.13 % Fe_2O_3 , 1.11 % K_2O , 0.33 % Na_2O , 0.18 % TiO_2 , and 6.37 % SO_3 .

Natural limestone (*Granit Pescar, Ljig, Serbia*), with a medium size of 250 μm was used as mineral filler. According to chemical analysis, it consists of: 54.86 % CaO, 0.21 % SiO₂, 1.10 % MgO, 0.5 % Al₂O₃, 0.09 % Fe₂O₃, 0.05 % K₂O, 0.005 % MnO, 0.5 % P₂O₅, and SO₂ in traces (LOI 43.64 %).

Fly ash, from Thermal Power Plant "Kolubara A", Serbia, was used in its original form for partial replacement of limestone. According to chemical analysis, it consists of: 58.60 % SiO₂, 21.92% Al₂O₃, 6.12 % CaO, 5.97 % Fe₂O₃, 1.77 % MgO, 1.50 % K₂O, 0.37 % Na₂O, and 0.49 % TiO₂ (LOI 3.09 %). Density of FA in the loose and compacted state was 690 kg/m³ and 910 kg/m³, respectively. The specific gravity was 2190 kg/m³.

Microstructure of FA was performed by SEM (scanning electron microscope), type JEOL JSM-5800 and the obtained microphotographs are given in Figure 1.

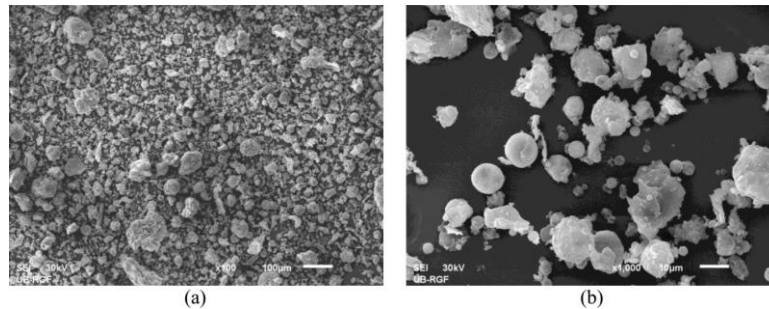


Figure 1. SEM microphotographs of fly ash taken at magnification of: a) 100 x, b) 1000 x

As seen in Figure 1, FA particles are generally spherical. Since only organic matter is lost during coal combustion, the inorganic residue remains in the ash. A large number of irregularly shaped particles is evidently present.

A polycarboxylate (Glenium Sky 690, *BASF Construction Chemicals, Italy*) additive was used as a superplasticizer that enables self-compacting capacity and improves the flowability of concrete.

The compositions of designed four SCC mixtures are shown in Table 1.

The reference SCC mixture E contains only limestone as filler. Other three SCC mixtures were made with partial replacement of FA in regard to the limestone amount: FA-10 with 10 mass. % of FA, FA-20 with 20 mass. % of FA and FA-50 with 50 mass. % of FA and with increased superplasticizer content necessary to provide workability.

Table 1. Design of SCC mixtures

	E	FA-10	FA-20	FA-50
Coarse aggregate (8-16mm) (kg/m ³)	430	430	430	430
Coarse aggregate (4-8mm) (kg/m ³)	430	430	430	430
Fine aggregate (0-4mm) (kg/m ³)	840	840	840	840
Cement C (kg/m ³)	380	380	380	380
Water W (kg/m ³)	183	183	183	183
Limestone powder LP (kg/m ³)	220	198	176	110
Fly ash FA (kg/m ³)	0	22	44	110
Superplasticizer (kg/m ³)	7.6	7.6	7.6	11.4
Water- to- cement ratio W/C	0.482	0.482	0.482	0.482

Each SCC mixture was proportioned by weight. A laboratory concrete mixer with a capacity of 60 l, fixed drum, and paddles at the vertical axel was used. The aggregate was mixed for one minute in a mixer, then the filler and cement were added and mixed for 30 s. Afterwards, water with the

superplasticizer was added and mixing continued until homogeneity (270 s). The preparation was realized at the ambient temperature (20-22 °C).

After preparation, rheological tests in fresh state of SCC were made.

Subsequently, casting was done. The specimens were removed from the molds after 24 h, and then cured in water until tests on hardened concrete were done. Each of the data obtained from testing corresponds to an average of at least three measurements.

2.2 Characterization of the SCC

The characterization of the **fresh state** of the produced SCC was performed by standard determination of density, entrained air content, flowability (Slump flow, Slump flow time (t_{500}), V-funnel time (t_v)), passing ability (L-box), and segregation resistance [10-14].

Investigations on the **hardened** SCC included: density, mechanical strength, static modulus of elasticity, water permeability, resistance against freezing in the presence of de-icing salt, and SEM analysis. Density was tested on prisms 12x12x36 cm up to the age of 180 days [15]; compressive strength on cubes at each age (3, 7, 14, 21, 28, 63, 90 and 180 days) [16]; three point bending (flexural strength) test on prisms 12x12x36 cm at the age of 28 days [17], static modulus of elasticity on cylinders with diameter of 15 cm and height of 30 cm, at the ages of 28 and 180 days [18]; water penetration at the older age of 63 days [19]; resistance against freezing in the presence of de-icing salt (3 % aqueous solution of NaCl) on special samples with the bottomless container on the top at the age of 28 days [20]. For the microstructure characterization, statistically representative samples of all mixtures were prepared and tested using the SEM (scanning electron microscope), type JEOL JSM-5800.

The SCC samples were kept in water for 180 days. They were periodically removed from water to perform measurements.

The performed qualitative analysis included comparison of the reference mixture E with the mixtures containing FA in terms of their porosity and structure.

3 Results and Discussion

3.1 Fresh SCC tests

The results of characteristic rheological tests on SCC are presented in Table 2.

According to the EFNARC, all SCC series with FA meet the requirements for the determined fresh state properties except the viscosity of FA-50. SCCs with FA exhibit lower workability than E, which is manifested in flowability and passing ability decrease as well as in segregation resistance increase. It can be concluded that the addition of FA in the higher proportion affects negatively the fluidity and workability of SCC.

Table 2. Fresh state properties of SCCs

	E	FA-10	FA-20	FA-50
Density (kg/m ³)	2397	2391	2370	2347
Entrained air content (%)	1.9	1.5	2.0	2.8
Slump flow (mm)	761.2	701.2	663.8	702.5
Slump flow time t_{500} (s)	2.62	5.71	10.91	11.32
V-funnel time t_v (s)	9.73	15.92	22.46	27.21
Passing ability L-box (H2/H1)	0.97	0.92	0.92	0.95
Segregation factor (%)	3.5	3.0	2.0	1.7

t_{500} - time required for spreading; t_v - V-funnel time; H1 and H2-heights at the beginning and at the end of the horizontal part of L-box, respectively

3.2 Hardened SCC tests

Density

Density values of tested series up to the age of 180 days are in the range of 2350-2420 kg/m³. Figure 2 shows the density change versus the logarithm of time.

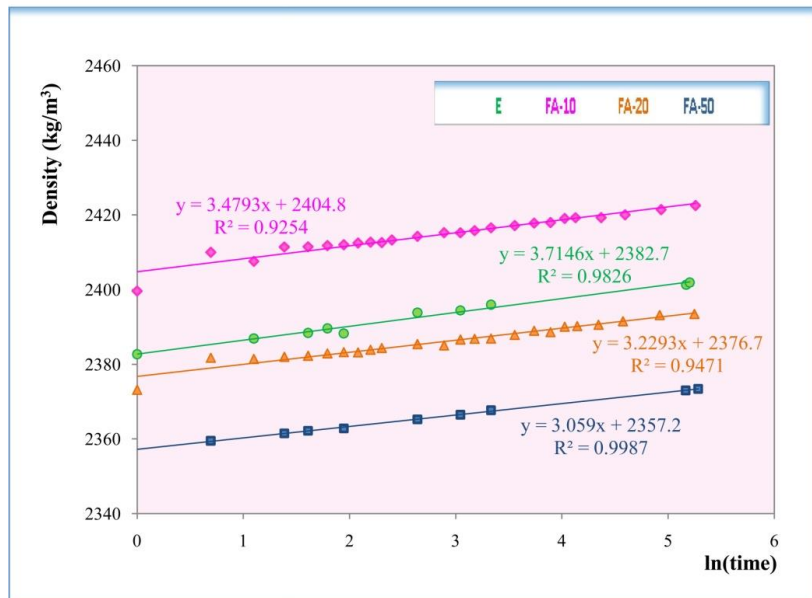


Figure 2. Density change of hardened SCCs versus time

As seen in Figure 2, at all ages, FA-50 exhibited the lowest density values, and FA-10 the highest. Unexpectedly, the density of FA-10 was higher than that of E, which is probably the result of measuring errors. Linear regression analysis gave equations with high values of correlation coefficients. Obviously, E has the greatest slope, and thus the fastest water absorption, which is in accordance with the fact that the FA addition improves the concrete structure resulting in lower water absorption [21]. Comparing only mixtures with FA, FA-10 has the greatest slope, followed by FA-20 and finally by FA-50.

Mechanical strength

The compressive strength is a basic property of hardened concrete and is often used as its quality indicator [22]. The obtained results of compressive strength are given in Figure 3.

As seen in Figure 3, the increase in FA amount leads to compressive strength decrease of SCCs at early ages and to strength increase at older ages. This is explained by the pozzolanic effect, which is more pronounced for larger FA quantities and older ages. 50 % of FA leads both to strength increase and decrease depending on age. This can be attributed to the negative effect of the mechanically weaker FA grains, especially coarser inhomogeneous, apart from the positive pozzolanic impact. However, LP-50 showed higher strength than E at all ages- from 4.3% at the age of 90 days to 16.5% at the age of 63 days. In this respect, a clear positive effect of using FA is evident. These results show that the addition of FA results in strength increase at all ages depending on its amount compared with the strength of E.

At the age of 28 days mixtures FA-10, FA-20, and FA-50 reached significantly higher strengths than E; precisely, higher for 11.3 %, 16.8 %, and 12.9 %, respectively. The 16.8 % increase for FA-20 in relation to E at 28 days of age is at the same time the largest difference among all data. This strength increment with the increasing FA content can be explained by the pozzolanic effect, which is more pronounced for larger FA quantities and at later ages.

Based on the analysis performed, a positive effect of the use of FA in SCCs is evident.

For concrete with FA, the rate of compression strength increment depends on a number of factors. Since FA, with the total content of oxides SiO₂ + Al₂O₃ + Fe₂O₃ over 80 % was used, the effect of a later increase in the concrete strength (but also a slower strength development at early ages) can be expected due to its pozzolanic reaction [23].

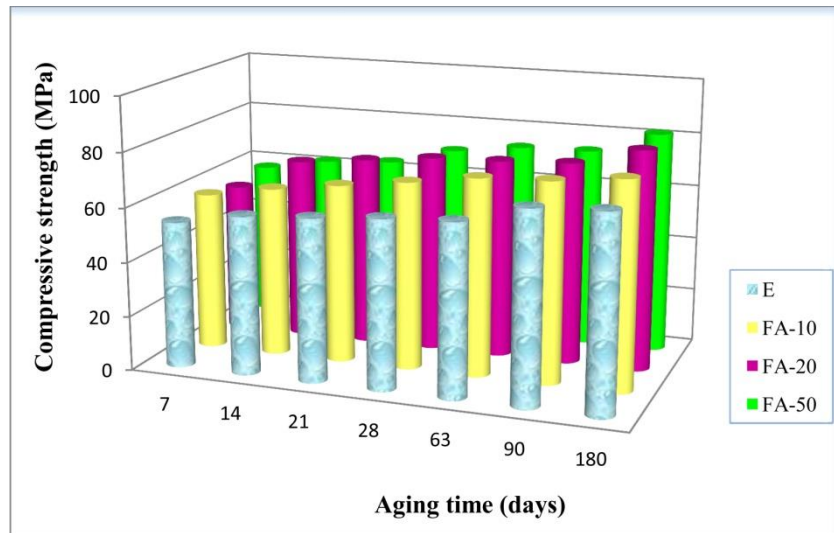


Figure 3. Compressive strength of SCC mixtures during time

Figure 4 shows the compressive strength increment of SCCs versus logarithm of time. A family of curves described by equations with high correlation coefficients was obtained by regression analysis.

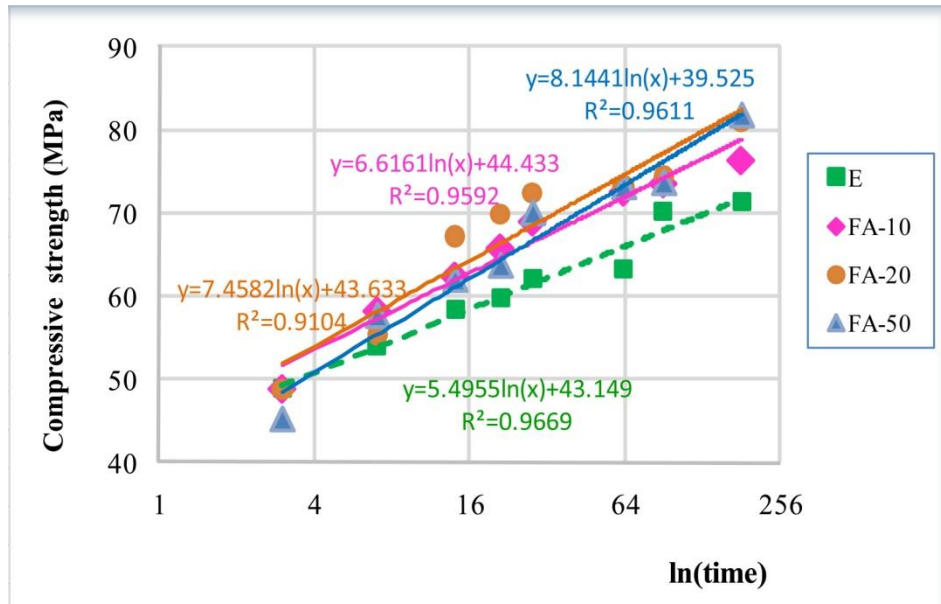


Figure 4. Compressive strength increment of SCC mixtures during the aging time

It can be observed that E represents the lower boundary of the curve family, while FA-20 the upper boundary line of the formed functional dependency family. The functional regressions derived for FA-10 and FA-50, from lower to higher, are between the two boundaries. In terms of the cement stone hardening, where the cement hydration and the pozzolanic reaction are involved, the rate of compressive strength increment, and thus the rates of the corresponding chemical reactions, can be interpreted by the slopes of the created lines. Namely, the slopes of all lines are positive- its lowest value is for E, which corresponds to the slowest rate of strength increment. A slope increment for SCCs containing FA is evident with FA content increase, which corresponds to the pozzolanic contribution to the strength enhancement. At some moment, due to the pozzolanic reaction, further significant strength increase for mixtures with FA, especially of FA-50, can be expected.

The flexural strength results for SCCs at the age of 28 days are given in Table 3.

As can be seen from Table 3, FA-10 had a 1 % lower flexural strength compared to E. FA-20 and FA-50, showed a slight flexural strength increase compared to E- 12 % and 3 %, respectively. Regarding flexural strength, the optimum FA content is 20 %.

Table 3. Flexural strength of SCC mixtures at the age of 28 days

	<i>E</i>	<i>FA-10</i>	<i>FA-20</i>	<i>FA-50</i>
Flexural strength f_{zs} [MPa]	10.3	10.2	11.5	10.6

Static elasticity modulus

The static elasticity modulus results for SCCs at the ages of 28 and 180 days are shown in Table 4.

Table 4. Static modulus of elasticity E_s [GPa] of SCCs at the ages of 28 and 180 days

Age (days)	<i>E</i>	<i>FA-10</i>	<i>FA-20</i>	<i>FA-50</i>
28	34.1	35.6	35.7	37.3
180	38.5	35.6	41.9	39.4

FA-10, *FA-20* and *FA-50*, at 28 days of age showed higher static elasticity modulus than *E*- 4.4 %, 4.5 % and 9.4 %, respectively. Similarly, at 180 days of age, *FA-10*, *FA-20* and *FA-50*, showed higher values than *E*- 8.1 %, 8.8 % and 2.3 %, respectively. Based on these results, and the evident elasticity modulus drop for *FA-50* at the age of 180 days, it can be concluded that lower *FA* content provides better elasticity at older ages.

Water permeability

Maximal and average depths of water penetration for each specimen of each mixture, as well as the average values for each mixture are given in Table 5.

Table 5. Depths h [mm] of the water penetration

Specimen	<i>E</i>		<i>FA-10</i>		<i>FA-20</i>		<i>FA-50</i>	
	Aver.	Max	Aver.	Max	Aver.	Max	Aver.	Max
1	8	16	10	15	9	14	11	15
2	9	16	9	17	10	15	10	17
3	11	17	9	16	11	17	9	15
Average value:	9.3	16.3	9.3	16.0	10.0	15.3	10.0	15.7

It is evident that all mixtures exhibited a similarly high level of water impermeability.

Resistance against freezing in the presence of de-icing salt

Mass loss for each mixture as well as damage depth after 25 cycles of simultaneous exposure to frost and 3 % aqueous solution of NaCl is presented in Table 6.

Table 6. Mass loss and damage depth for SCC mixtures

	Mass loss (mg/mm^2)	Damage depth (mm)
<i>E</i>	0.12	0.6
<i>FA-10</i>	0.09	0.4
<i>FA-20</i>	0.10	0.4
<i>FA-50</i>	0.10	0.5

Frost resistance testing has shown some advantages concerning fly ash addition to SCC mixtures and also its contribution to improving durability in the salt environment.

The mixtures with FA after treatment underwent a certain mass loss, but lower than E. A similar effect is observed regarding the damage depth, with optimum effects for FA-10.

SEM analysis

Representative samples of all SCCs were prepared for the structure characterization by the use of SEM. Basically, the performed analysis had qualitative character.

Based on the SEM analysis, it can be observed that the homogeneity was achieved in all SCC mixtures, while the porosity was visually similar (Figure 5). Furthermore, although the contact of aggregate grains and the cement matrix is generally good, it should be noticed that this contact is better for certain grains (sandstone, limestone) than for others (quartzite), owing to the surface character and compactness of the aggregate grains themselves.

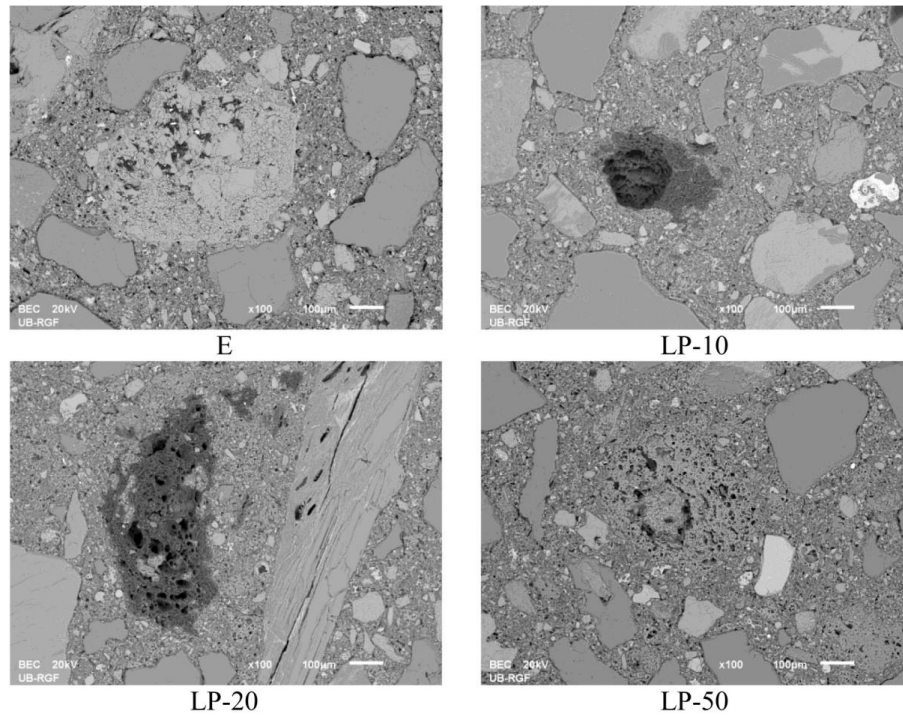


Figure 5. SEM microphotographs of SCC series

4 Conclusion

In compliance with the trends of promoting sustainable development in the field of construction, the possibility of using industrial byproduct- FA for partial substitution of the mineral filler-limestone in SCC was investigated. SCCs with the addition of FA were examined and compared with the reference mixture with limestone in order to optimize the properties and composition of these concretes.

All SCCs with FA met the standards concerning fresh state properties except the viscosity of FA-50.

Regarding hardened SCC properties, positive effect of FA is evident. Lower amounts of FA led to compressive strength increase, which was especially pronounced for FA-20 and at older ages. Flexural strength values were similar. The SCCs with FA exhibited better resistance against freezing in the presence of de-icing salt and higher values of static elasticity modulus than the reference mixture. All mixtures have similarly high impermeability and hence compactness, which was proved by SEM. Based on the SEM analysis, it can be concluded that homogeneity was achieved in all mixtures, while the porosity was visually similar. High degree of compactness of SCCs with FA is an an indicator of good durability.

This study showed that it is possible to obtain a high-performance SCC using FA and that its optimal content is 20 % with respect to the total filler mass.

It is of great importance for the construction industry and should be continued towards the practical application of the designed SCC mixtures. This application may include testing of structural

elements (beams and columns) in laboratory conditions, as well as the design of construction systems in the field and their monitoring as part of full-scale feasibility studies.

Research can be widened to designing new mixtures with a higher proportion of FA as a mineral additive, which would raise the valorization of this industrial by-product in Serbia to a larger scale.

5 Acknowledgments

This work was financially supported by the Ministry of Education, Science and Technological Development of the Republic of Serbia (Grant No. 451-03-68/2020-14/200026 IHTM, 92166/3-19, 451-03-68/2020-14/20002, 451-03-68/2020-14/200135)

6 References

- [1] **Jevtić, D., Zakić, D., Savić, A., Radević, A.,** The influence of fly ash on basic properties of mortar and concrete, Proceedings Scientific conference Planning, design, construction and building renewal, Novi Sad, Serbia, 2012.
- [2] **Jevtić D., Markičević, J., Savić, A.,** Fly Ash Influence on Certain Properties of Concrete Composites, Proceedings 6th International Conference Science and Higher Education in Function of Sustainable Development, Užice, Serbia, 2013.
- [3] **Jevtić, D., Mitrović, A., Savić, A.,** Experimental investigation of fly ash content influence on cement mortars properties, Proceedings 2nd International Symposium on Environmental and Material Flow Management, Zenica, Bosnia and Hercegovina, 2012.
- [4] **Okamura, H.,** Self-compacting high-performance concrete, *Concrete International* 19 (1997), 7, pp. 50-54.
- [5] **Wesche, K.,** Fly Ash in Concrete: Properties and performance (Rilem Report 7), Report of Technical Committee 67-FAB Use of Fly Ash in Building, Taylor & Francis e-Library, 2005
- [6] **Jevtić, D., Savić, A., Radević, A.,** Fly ash influence on concrete composites - Contribution to sustainable construction, Proceedings 15th YuCorr, Tara, 2013.
- [7] **Jevtić, D., Zakić, D., Savić, A.,** Cementitious Composites Made With Fly Ash - A Contribution To The Sustainable Civil Engineering, Proceedings 14th International Conference Research and Development in Mechanical Industry, Topola, Serbia, 2014.
- [8] **Jevtić, D., Zakić, D., Savić, A., Radević, A.,** Properties modeling of cement composites made with the use of fly ash, Book of abstracts III International Congress Engineering, Environment and Materials in Processing Industry, Jahorina, Bosnia and Herzegovina, 2013.
- [9] **Jevtić, D., Zakić, D., Savić, A., Radević, A.,** Properties modeling of cement composites of fly ash, *Materials Protection, LV*, (2014), pp. 39-44.
- [10] *** SRPS EN 12350-6:2010 Testing fresh concrete - Part 6: Density.
- [11] *** SRPS EN 12350-7:2010 Testing fresh concrete - Part 7: Air content - Pressure methods.
- [12] *** SRPS EN 206-1:2011 Concrete - Part 1: Specification performance, production and conformity.
- [13] *** SRPS EN 12350-10:2012 Testing fresh concrete - Part 10: Self-compacting concrete - L box test.
- [14] *** SRPS EN 12350-11:2012; Testing fresh concrete - Part 11: Self-compacting concrete - Sieve segregation test.
- [15] *** SRPS EN 12390-7:2010 Testing hardened concrete – Part 7: Density of hardened concrete
- [16] *** SRPS EN 12390-3:2010 Testing hardened concrete - Part 3: Compressive strength of test specimens.
- [17] *** SRPS ISO 4013:2000 Concrete - Determination of flexural strength of test specimens
- [18] *** ASTM C469/ C469M 10: Standard Test Method for Static Modulus of Elasticity and Poisson's Ratio of Concrete in Compression, (2005).
- [19] *** SRPS U.M1.015:1998 Concrete - Hardened concrete - Determination of the depth of penetration of water under pressure.
- [20] *** SRPS U.M1.055:1984 Concrete - Method of test for resistance of concrete against freezing

- [21] **Assie, S., Escadeillas, G., Marchese, G., Waller, V.**, 2006. Durability properties of low-resistance self compacting concrete, Magazine of Concrete Research 58 (2006), 1, pp. 1-7.
- [22] **Muravljev, M.**, Osnovi teorije i tehnologije betona, Građevinska knjiga, Beograd, 2011.
- [23] ASTM C 618: Standard specification for coal fly ash and raw or calcined natural pozzolan for use in concrete, (2003).