

**University of Belgrade, Technical faculty in Bor
Chamber of Commerce and Industry of Serbia**

PROCEEDINGS

2021 IMPRO 

INTERNATIONAL MINERAL PROCESSING & RECYCLING CONFERENCE

**XIV INTERNATIONAL MINERAL
PROCESSING AND RECYCLING
CONFERENCE**

Editors:

Jovica Sokolović

Milan Trumić

May 12-14, 2021, Belgrade, Serbia





UNIVERSITY OF
BELGRADE



CHAMBER OF
COMMERCE AND
INDUSTRY OF SERBIA

**University of Belgrade, Technical faculty in Bor
Chamber of Commerce and Industry of Serbia**

PROCEEDINGS



XIV International MINERAL PROCESSING and RECYCLING CONFERENCE

Editors:

Jovica Sokolović

Milan Trumić

May 12 – 14, 2021, Belgrade, Serbia

**XIV INTERNATIONAL
MINERAL PROCESSING and RECYCLING CONFERENCE**

PUBLISHER:

University of Belgrade, Technical Faculty in Bor

FOR THE PUBLISHER:

DEAN: Prof. Dr Nada Štrbac

EDITORS:

Prof. Dr Jovica Sokolović

Prof. Dr Milan Trumić

PROCEEDINGS COVER DESIGN:

Branislav Gapić

PRINTED BY:

Tercija d.o.o., Bor, Serbia

Printed: 100 copies

PUBLICATION YEAR:

2021

=====

CIP - Каталогизација у публикацији
Народна библиотека Србије, Београд

622.7(082)

502.131.1:628.477.6(082)

628.477.6(082)

INTERNATIONAL Mineral Processing and Recycling Conference (14 ; 2021 ; Beograd)

Proceedings / XIV International Mineral Processing and Recycling Conference, IMPRC, May
12-14, 2021, Belgrade, Serbia ; editors Jovica Sokolović, Milan Trumić. - Bor : University of
Belgrade, Technical Faculty, 2021 (Bor : Tercija). - XI, 514 str. : ilustr. ; 25 cm

Na vrhu nasl. str.: Chamber of Commerce and Industry of Serbia. - Tiraž 100. - Bibliografija uz
svaki rad. - Registar.

ISBN 978-86-6305-113-3

а) Руде -- Припрема -- Зборници б) Отпадне материје -- Одрживи развој -- Зборници в)
Отпадне материје -- Рециклажа -- Зборници

COBISS.SR-ID 37464585

=====



**Conference is financially supported by
Republic of Serbia,
Ministry of Education, Science and
Technological Development**

SCIENTIFIC COMMITTEE

Prof. Dr Milan Trumić, Serbia, President
Prof. Dr Grozdanka Bogdanović, Serbia, Vice President
Prof. Dr Jovica Sokolović, Serbia, Vice President
Prof. Dr Mauricio Torem, Brazil
Prof. Dr Sanja Miskovic, Canada
Prof. Dr Qingqing Huang, USA
Prof. Dr Zhiyong Gao, China
Prof. Dr Wencheng Xia, China
Prof. Dr Takashi Nakamura, Japan
Prof. Dr Boris Albijanic, Australia
Prof. Dr Raghupatruni Bhima Rao, India
Prof. Dr Przemyslaw Kowalczyk, Norway
Prof. Dr Junbeum Kim, France
Prof. Dr Srećko Stopić, Germany
Prof. Dr Alejandro Rodriguez Pascual, Spain
Prof. Dr Adele Muscolo, Italy
Prof. Dr Georgios Anastassakis, Greece
Prof. Dr Mehmet Polat, Turkey
Prof. Dr Leonid Vaisberg, Russia
Prof. Dr Vladimír Čablik, Czech Republic
Dr Slavomir Hredzak, Slovakia
Prof. Dr Gabor Musci, Hungary
Prof. Dr Francisc Popescu, Romania
Prof. Dr Ivan Nishkov, Bulgaria
Prof. Dr Jakob Lamut, Slovenia
Prof. Dr Aleksandra Anić Vučinić, Croatia
Prof. Dr Ilhan Bušatlić, Bosnia & Herzegovina
Prof. Dr Svjetlana Sredić, Republic of Srpska, Bosnia & Herzegovina
Prof. Dr Mirjana Golomeova, North Macedonia
Prof. Dr Nada Štrbac, Serbia
Prof. Dr Milan Antonijević, Serbia
Prof. Dr Miodrag Žikić, Serbia
Prof. Dr Zoran Stević, Serbia
Prof. Dr Dejan Tanikić, Serbia
Prof. Dr Snežana Šerbula, Serbia
Prof. Dr Mira Cocić, Serbia
Prof. Dr Ljubiša Andrić, Serbia

Prof. Dr Milena Kostović, Serbia
Prof. Dr Aleksandar Jovović, Serbia
Prof. Dr Željko Kamberović, Serbia
Prof. Dr Vlada Veljković, Serbia
Prof. Dr Goran Vujić, Serbia
Prof. Dr Jelena Radonić, Serbia
Prof. Dr Srđan Rončević, Serbia
Prof. Dr Irma Dervišević, Serbia
Prof. Dr Marina Stamenović, Serbia
Prof. Dr Vladimir Pavićević, Serbia
Prof. Dr Zoran Štirbanović, Serbia
Prof. Dr Maja Trumić, Serbia
Dr Miroslav Ignjatović, Serbia
Dr Ivana Smičiklas, Serbia
Dr Miroslav Sokić, Serbia
Dr Dragan Radulović, Serbia
Dr Vladan Milošević, Serbia
Dr Sonja Milićević, Serbia
Dr Milinko Radosavljević, Serbia
Dr Mile Bugarin, Serbia
Dr Zoran Stevanović, Serbia
Dr Radmila Marković, Serbia

ORGANIZING COMMITTEE

Prof. Dr Jovica Sokolović, Serbia, President
Prof. Dr Milan Trumić, Serbia
Prof. Dr Grozdanka Bogdanović, Serbia
Dr Miroslav Ignjatović, Serbia
Prof. Dr Zoran Štirbanović, Serbia
Prof. Dr Maja Trumić, Serbia
MSc Vladimir Nikolić, Serbia
MSc Dragana Marilović, Serbia
MSc Predrag Stolić, Serbia
MSc Katarina Balanović, Serbia
BSc Ivana Ilić, Serbia
BSc Sandra Vasković, Serbia
BSc Slavica Stevanović, Serbia
Dobrinka Trujić, Serbia

TABLE OF CONTENTS

PLENARY LECTURES	1
Zhiyong Gao, Mengjie Tian, Jianyong He, Wanjia Zhang, Wei Sun, Jian Cao ATOMIC FORCE MICROSCOPY (AFM) FORCE MEASUREMENT IN SURFACE CHEMISTRY OF MINERAL FLOTATION	3
Aleksandar Jovović, Danijela Božanić, Goran Vujić WASTE AND WASTEWATER MANAGEMENT AS A POTENTIAL FOR REDUCTION OF GHG EMISSIONS	11
SECTION LECTURES	17
Zoran Stevanović, Peter Bayer, Stefan Kamsties, Radmila Marković, Vojka Gardić, Aleksandar Doderović, Nikola Stanić APPROACH FOR SOLVING ENVIRONMENTAL ISSUES AT ABANDONED MINING WASTES IN REPUBLIC OF SERBIA	19
Ivana Smičiklas, Mihajlo Jović, Marija Egerić, Marija Šljivić-Ivanović, Slavko Smiljanić AVAILABILITY OF ESSENTIAL AND TRACE METALS IN AN ACIDIC SOIL AMENDED WITH BAUXITE RESIDUE (RED MUD)	27
Nemanja Stanisavljević, Nikolina Tošić, Bojan Batinić, Isidora Berežni FUTURE QUESTIONS FOR RECYCLING SOCIETIES	33
PAPERS BY SECTIONS	35
Arun Kumar Jena, Satya Sai Srikant, Shiv Kumar Angadi, Raghupatruni Bhima Rao COMMUNITION CHARACTERISTICS OF IRON ORES	37
Vladimir Nikolić, Milan Trumić, Juan Maria Menéndez-Aguado DETERMINATION OF BOND WORK INDEX IN NON-STANDARD MILLS	43
Katarina Balanović, Milan Trumić, Maja Trumić EXPERIMENTAL STUDY ON THE GRINDING RATE CONSTANT OF QUARTZ IN A BALL MILL	50
Nemanja Bogdanović, Milan Trumić MONITORING THE GRINDING KINETICS IN BALL MILL WITH DIFFERENT SIZE BALL	56
Maja Trumić, Milan Trumić, Grozdanka Bogdanović, Ljubiša Andrić INFLUENCE OF GRAIN DENSITY AND SHAPE ON THE SCREENING RATE CONSTANT VALUE	61
Nikola Đokić, Lazar Kričak, Stefan Milanović, Marinko Pavlović, Stefan Krstić THE IMPACT OF LIMESTONE FRAGMENTATION ON RAW MIX PRODUCTION IN CEMENT INDUSTRY	66
Nataša Đorđević, Slavica Mihajlović, Milica Vlahović, Sanja Martinović APPLICATION OF MECHANOCHEMICALLY ACTIVATED SODIUM CARBONATE IN ENVIRONMENTAL PROTECTION	72
Galina Dvoichenkova, Evgeny Kovalenko, Valery Morozov, Yuri Podkamenny DESTRUCTION OF CRYSTALLINE MINERAL COATINGS ON THE SURFACE OF DIAMONDS WITH THE USE OF THERMAL AND ELECTROCHEMICAL TREATMENT	78

Valentine Chanturiya, Igor Zh. Bunin, Maria Ryazantseva THE ALTERATIONS OF THE CALCIFEROUS MINERALS SURFACE AND DIRECTED AJUSTMENT OF THE FLOATABILITY THROUGH THE APPLICATION OF HIGH - POWER ELECTROMAGNETIC PULSES	84
Kyriakos Syrmakezis, Konstantinos Tsakalakis EFFECT OF GAS RATE AND PRESSURE IN THE GAS HOLDUP IN A LABORATORY FLOTATION COLUMN	93
Valery Morozov, Irina Pestriak, Erdenezul Jargalsaikhan OPTIMIZING THE FLOTATION OF COPPER-MOLYBDENUM ORES USING THE ABSORPTION CAPACITY OF ORE TO THE COLLECTOR	100
Zoran Petkovic NEW REAGENT AND METHOD FOR SELECTIVE FLOATING OF CLAYS IN THE CONCENTRATION PROCESS OF NON-FERREOUS MINERALS	106
Vladimir Riaboy, Vitaly Kretov, Sergei Levkovets, Iliia Riaboy, Ekaterina Smirnova APPLICATIONS OF A NEW THIOAMIDE GROUP COLLECTOR IN SULFIDE ORE FLOTATION	114
Maria Sinche-Gonzalez, Daniel Fornasiero EFFECT OF SULPHATE IN MINING-PROCESS WATER ON SULPHIDE FLOTATION	120
Kadriann Tamm, Zeinab Arab Zadeh, Xiaosheng Yang FROTH FLOTATION STUDIES FOR BENEFICIATION OF ESTONIAN PHOSPHATE ROCK	130
Nedeljko Magdalinović, Zoran Štirbanović, Dragiša Stanujkić, Jovica Sokolović SELECTION OF COPPER-PYRITE FLOTATION CIRCUIT DESIGN BY APPLYING THE PREFERENCE SELECTION INDEX METHOD	136
Grozdana Bogdanović, Maja Trumić, Zoran Stevanović VALORIZATION OF COPPER FROM LOW-GRADE ORE BY LEACHING: INFLUENCE OF SULPHURIC ACID CONCENTRATION	142
Miljan Marković, Milan Gorgievski, Nada Štrbac, Dragana Božić, Velizar Stanković, Vesna Grekulović, Milica Zdravković KINETIC STUDY OF COPPER IONS BIOSORPTION ONTO BARLEY STRAW	148
Mladen Bugarčić, Dragana Milošević, Miroslav Sokić, Gvozden Jovanović, Zorica Lopičić, Aleksandar Marinković, Milan Milivojević SYNTHESIS AND CHARACTERIZATION OF COBALT FERRITE/EXPANDED VERMICULITE AS A SORBENT OF NICKEL IONS	154
Dragana Medić, Snežana Milić, Slađana Alagić, Silvana Dimitrijević, Stefan Đorđievski, Maja Nujkić, Aleksandra Papludis INFLUENCE OF pH VALUE OF LEACH SOLUTIONS ON EFFICIENCY OF ELECTROLYTIC DEPOSITION OF COBALT	160
Gizem Hacıoğlu, Kaia Tõnsuaadu, Kristjan Urtson, Toivo Kallaste, Andres Trikkel DISSOLUTION OF RARE EARTH ELEMENTS FROM PHOSPHATE ORE IN HYDROCHLORIC ACID	166
Slavomir Hredzák, Marek Matik, Oľga Šestinová, Anton Zubrik, Daniel Kupka, Silvia Dolinská, Ingrid Znamenáčková POSSIBILITIES OF EOLIAN SANDS GRAVITY UPGRADING FROM THE ŠAJDÍKOVE HUMENCE DEPOSIT (WEST SLOVAKIA)	172

Milena Kostović, Nina Pantelić POSSIBILITY OF CLEANING OF BURNING COAL FROM SURFACE MINING	179
Sanjay Chaudhuri, Uday Sankar Chattopadhyay, Subash Maji, Thonangi Gouri Charan BENEFICIATION OF NON COKING COAL FROM OPEN CAST MINES OF WESTERN COALFIELD AREA FOR VALUABLE UTILIZATION	184
Mehmet Bilen CORRELATION BETWEEN IMAGE ANALYSIS AND CALORIFIC VALUES OF COALS	190
Serdar Yilmaz, İhsan Toroglu, Dilek Cuhadaroglu, Anna Rasskazova PREDICTION OF CALORIFIC VALUE FOR SOME TURKISH LIGNITES BASED ON MOISTURE AND ASH CONTENT	196
Jovica Sokolović, Slobodan Mitić, Ivana Ilić A COMPARISON OF SEPARATION EFFICIENCY OF RAW AND WASTE COALS IN A COAL SEPARATION PLANT IN THE ANTHRACITE COAL MINE "VRŠKA ČUKA"	202
Ljiljana Tankosić, Svjetlana Sredić COMPARISON OF THE INFLUENCE OF POLYACRYLAMIDE AND SODIUM OLEATE ON SELECTIVE FLOCCULATION OF GETITE FROM SLUDGE	208
Aleksandr Nikolaev, Sergey Avksentiev, Raul Izquierdo Pupo, Alberto Turro Breff RESEARCH ON REGIMES OF LIMONITE ORE HYDROTRANSPORT FOR THE CONDITIONS OF PERDO SOTO ALBA PLANT	214
Andrey Goryachev PROCESSING OF SULFIDE COPPER-NICKEL RAW MATERIALS BY LOW-TEMPERATURE ROASTING WITH AMMONIUM SULFATE	223
Sibel Gezer A CRITICAL ASSESSMENT OF URANIUM RESOURCES OF TURKEY	229
Branislav Stakić, Bojana Maksimović, Dejan Ćirić POTENTIAL MINERAL RESOURCES OF THE ANTHRACITE MINE „VRŠKA ČUKA,, AVRAMICA	234
Ilker Acar UTILIZATION POTENTIAL OF A SERPENTINE-RICH SAMPLE AS A REFRACTORY RAW MATERIAL	240
Ilker Acar HEXAVALENT CHROMIUM ANALYSIS OF A FERROCHROME SLAG	245
Vladimir Topalović, Srđan Matijašević, Snežana Grujić, Veljko Savić, Jelena Nikolić, Sonja Smiljanić, Snežana Zildžović THERMAL PROPERTIES OF LITHIUM GERMANATE PHOSPHATE GLASS STUDIED BY DTA	251
Džafer Dautbegović, Mirsada Hasanbašić ANALYZE OF MUNICIPAL WASTE MORPHOLOGY	257
Angelina Pavlović, Goran Bošković, Nebojša Jovičić MATERIAL FLOW ANALYSIS OF GLASS PACKAGING WASTE IN THE REPUBLIC OF SERBIA	263
Višnja Mihajlović, Jovanka Milićević IMPACT OF THE CIRCULAR ECONOMY AND EXTENDED PRODUCER RESPONSIBILITY (EPR) ON REDUCTION OF PACKAGING WASTE	271

Agapi Vasileiadou, Stamatis Zoras, Andreas Iordanidis REACTIVITY ASSESSMENT OF SEASONAL COMPOST OF MUNICIPAL SOLID WASTES (MSW) AND THEIR CO-COMBUSTION WITH LIGNITE VIA ACTIVATION ENERGY	275
Isidora Berežni, Bojan Batinić, Nemanja Stanisavljević, Francine Duarte Castro, Mentore Vaccari COMPARISON OF WEEE RECYCLING PRACTICE IN ITALY AND SERBIA	281
Vladan Joldžić LEGISLATION ASPECTS ON ENVIRONMENTAL PROTECTION AND WASTE MANAGEMENT ON THE EXAMPLE OF THE REPUBLIC OF SERBIA	292
Dragana Marilović, Maja Trumić EFFECT OF SODIUM DODECYL SULFATE IN DEINKING FLOTATION	298
Vesna Conić, Dragana Božić, Suzana Dragulović, Ljiljana Avramović, Radojka Jonović, Mile Bugarin RESEARCH ON ACID LEACHING OF Cu, Zn AND In FROM JAROSITE WASTE	304
Marija Šljivić-Ivanović, Mihajlo Jović, Slavko Smiljanić, Ivana Smičiklas ANALYSIS OF THE EFFECTS OF THE VARIABLES IN THE PROCESS OF CADMIUM SEPARATION BY SEASHELL WASTE	310
Dragana Božić, Radmila Marković, Zoran Stevanović, Daniela Dascalu, Vulpe Bianca, Mariana Adina Matica DIFFERENT NEUTRALIZING AGENTS USED FOR TREATMENT OF ACID MINE WATER	316
Ljiljana Avramović, Radojka Jonović, Vanja Trifunović, Vojka Gardić, Mile Bugarin, Mariana Adina Matica, Gheorghiu Menghiu METAL RECOVERY FROM SLUDGE OBTAINED DURING THE NEUTRALIZATION PROCESSES OF AMD WATER	322
Vojka Gardić, Zoran Stevanović, Radmila Marković, Ljiljana Avramović, Radojka Jonović, Dragana Božić, Jelena Petrović, Renata Kovačević, Ljubiša Obradović, Vanja Trifunović, Bianca Boros, Adriana Isvoran, Vasile Ostafe STABILIZATION AND CHARACTERIZATION OF THE SOLID WASTE GENERATED IN NEUTRALIZATION SLUDGE LEACHING PROCESS	328
V. Aishvarya, Barsha Marandi, Abdul Rauf Sheik, Indra Narayan Bhattacharya, Kali Sanjay PRODUCTION OF ELECTROLYTIC MANGANESE DIOXIDE (EMD) FOR Li ION BATTERY APPLICATIONS FROM SECONDARIES	334
Marija Šljivić-Ivanović, Ivana Jelić, Slavko Dimović CEMENTITIOUS WASTE MATERIALS UTILIZATION IN RADIONUCLIDE IMMOBILIZATION BY SORPTION	339
Blagica Cekova, Viktorija Bezhovska, Filip Jovanovski APPLICATION OF FLOATING ASH TO GET PORTLAND CEMENT	345
Marinko Pavlović, Nikola Đokić, Taras Kulyk, Stefan Krstić EFFECT OF FUEL ASH ON RAW MIX IN CLINKER PRODUCTION	351
Veljko Savić, Vladimir Topalović, Jelena Nikolić, Srđan Matijašević, Snežana Zildžović, Snežana Grujić, Sonja Smiljanić DISSOLUTION OF GLASS MADE FROM COAL FLY ASH, GLASS CULLET AND CALCIUM CARBONATE	357
Irma Dervišević, Jovana Galjak, Ivica Ristović	

UTILIZATION OF SECONDARY RAW MATERIALS FROM MINE TAILINGS AND INDUSTRIAL LANDFILLS	363
Branko Despotović, Branka Dugić Kojić, Pero Dugić OPPORTUNITIES FOR CHOOSING RAW MATERIALS FOR ECOLOGICALLY ACCEPTABLE LUBRICANTS AND PRACTICAL EXPERIENCE	369
Marija Tasić, Jelena Jovanovic, Milan Kostić, Olivera Stamenković, Vlada Veljković TECHNO-ECONOMIC ANALYSIS OF CHERRY OIL BIODIESEL PRODUCTION	375
Jovana Bošnjaković, Vladimir Pavićević, Vesna Radojević, Jovica Sokolović ARSENIC REMOVAL FROM WATER BY ADSORPTION – A SHORT REVIEW	381
Radmila Marković, Ljubiša Obradović, Vojka Gardić, Renata Kovačević, Zoran Stevanović, Adriana Isvoran, Vladan Marinković CONTAMINATION OF RIVERS WATERCOURSES IN BOR DISTRICT WITH As AND Cd IONS	388
Snežana Šerbula, Jelena Kalinović, Jelena Milosavljević, Ana Radojević, Tanja Kalinović UNPRECEDENTED COPPER SMELTING ACTIVITY IN THE VERY CENTRE OF BOR – POOR AIR QUALITY	394
Žaklina Tasić, Ana Simonović, Marija Petrović Mihajlović, Milan Radovanović, Milan Antonijević INVESTIGATION OF THEOBROMINE USING A PENCIL GRAPHITE ELECTRODE	400
Jelena Milosavljević, Snežana Šerbula, Jelena Kalinović, Ana Radojević, Tanja Kalinović, Boban Spalović SPECIFIC SOIL ENZYME ACTIVITIES AND ENZYME-BASED SOIL QUALITY INDICES IN THE LONG-TERM POLLUTED ANTHROPOGENIC ECOSYSTEM	406
Ana Radojević, Snežana Šerbula, Jelena Kalinović, Jelena Milosavljević, Tanja Kalinović ASSESSMENT OF METAL(LOID) POLLUTION IN THE URBAN-INDUSTRIAL, TOURIST AND TRAFFIC ZONES OF BOR, USING COMON HAZEL	412
Jelena Kalinović, Snežana Šerbula, Jelena Milosavljević, Ana Radojević, Tanja Kalinović ASSESSMENT OF THE SOIL CONTAMINATION LEVEL IN BOR AND ITS SURROUNDINGS (SERBIA) BASED ON DIFFERENT POLLUTION INDICES	418
Slavica Mihajlović, Nataša Đorđević, Aleksandra Patarić, Marina Blagojev THE IMPACT OF MINERAL RESOURCES EXPLOITATION ON THE ENVIRONMENT	424
Aleksandra Papludis, Maja Nujkić, Snežana Milić, Dragana Medić, Slađana Alagić, Sonja Stanković INFLUENCE OF METALLURGICAL ACTIVITIES ON THE CONTENT OF MANGANESE, STRONTIUM AND CHROME IN CHICORY	430
Miomir Mikić, Sandra Milutinović, Miroslav Ilić, Ivan Jelić, Miloš Ilić DEGRADED AREAS RECULTIVATION ON LOCATION OF OPEN PIT ZAGRAĐE 5	436
Stefan Krstić, Marinko Pavlović, Nikola Đokić, Taras Kulyk REMEDICATION AND RECLAMATION OF DEGRADED AREA IN THE SOUTH-EASTERN PART OF THE MARLSTONE QUARRY "TREŠNJA"	442
Emina Požega, Danijela Simonović, Saša Marjanović, Milenko Jovanović, Zdenka	

Stanojević Šimšić, Slađana Krstić, Miomir Mikić THERMOELECTIC MATERIALS APPLICATION AND THEIR CONTRIBUTION TO PROVIDING CLEANER ENERGY	447
Milenko Jovanović, Miomir Mikić, Radmilo Rajković, Daniel Kržanović, Emina Požega HYBRID GEOMATERIALS	452
Lyubomir Ilchev, Nadezhda Davcheva-Ilcheva STRUCTURE, ORGANISATION AND FUNCTIONING OF A SUSTAINABLE DEVELOPING METALLURGICAL PLANT	459
Elisaveta Valova BIODIVERSITY CONSERVATION NEAR THE ADA TEPE MINE - MISSION POSSIBLE	466
Zoran Štirbanović, Zorica Trkulja, Sandra Vasković, Sanja Popović, Jelena Milutinović THE AWARENESS OF IMPORTANCE OF RECYCLING AMONG HIGH SCHOOL AND UNIVERSITY STUDENTS IN BOR	471
Aleksandra Jelić, Nebojša Ćurčić, Novak Milošević, Marina Stamenović, Marta Trninić, Slaviša Putić CURRENT METHODS AND MODELS IN PROCESS SAFETY AND RISK MANAGEMENT	477
Martina Petković, Anita Klikovac, Dragan Knežević, Biljana Nikolić THE IMPACT OF LANDSLIDES AND EROSIONS ON THE MULTI-RISK ASSESSMENT IN THE MUNICIPALITY OF SMEDEREVO	483
Martina Petković, Milenko Petrović, Dragan Knežević, Akaid Saradak ANALYSIS OF THE STABLE FIRE EXTINGUISHING SYSTEMS IN UNDERGROUND EXPLOITATION AND MINING	490
Miomir Mikić, Milenko Jovanović, Daniela Urošević, Radmilo Rajković NOISE SOURCES AND CONTROL IN UNDERGROUND METAL MINING	495
ABSTRACTS	501
Hamid Reza Shirazi, Hamid Khoshdast, Mohammad NaeimZeidabadi Nejad TROUBLESHOOTING OF THE SECONDARY VIBRATING SCREEN AT THE GOHAR- ZAMIN IRON ORE COMPLEX BY MONITORINGTHE 3D CLOGGING PATTERNS	503
Alireza Gholami, Mohammad NaeimZeidabadi Nejad, Hamid Khoshdast INTELLIGENT SIMULATION OF METALLURGICAL RESPONSE OF GOHAR-ZAMIN IRON ORE PROCESSING COMPLEX USING BIOGEOGRAPHY-BASED ANN METHOD	504
Bogoljub Vučković CADASTRE OF MINING WASTE FROM ABANDONED MINES IN SERBIA 2020, EU/IPA FUND - PRELIMINARY REMARKS	505
Cherifa Benzidane THE ROLE OF ALGERIAN LEGISLATION IN MANAGEMENT OF HEALTHCARE WASTE	506
Cherifa Benzidane THE STRATEGY OF UNITED ARAB EMIRATES IN DEVELOPING RENEWABLE ENERGIES	507
Marija Tasić, Katarina Stamenković, Milan Kostić, Olivera Stamenković, Vlada Veljković SIMULATION OF CHERRY OIL BIODIESEL PRODUCTION	508
AUTHORS INDEX	509

APPLICATION OF MECHANOCHEMICALLY ACTIVATED SODIUM CARBONATE IN ENVIRONMENTAL PROTECTION

Nataša Đorđević^{1#}, Slavica Mihajlović¹, Milica Vlahović², Sanja Martinović²

¹ Institute for Technology of Nuclear and Other Mineral Raw Materials,
Belgrade, Serbia

² University of Belgrade, Institute of Chemistry, Technology and Metallurgy,
Belgrade, Serbia

ABSTRACT – Sodium carbonate samples were mechanically activated in a vibro mill. The increase in the free surface area of the activated samples was monitored by the BET method, and the state of the crystal lattice by the diffraction method. The analysis of the results showed a significant increase in the free surface of the activated material as well as significant changes in the crystal structure of the samples due to grinding in a vibro mill. Such activation of sodium carbonate would enable a significant increase in the sorption properties of sodium carbonate and thus its application in environmental protection.

Keywords: Air Protection, Sodium Carbonate, Mechanochemical Activation.

INTRODUCTION

Due to the increasing pollution of the environment, there is a need for fast and efficient methods of prevention and solving the problem of ecological protection. Increasing the concentration of carbon dioxide in the atmosphere is one of the key parameters of nature pollution, which has multiple negative consequences for life on Earth. One of the most effective ways to maintain the concentration of CO₂ in the air is the natural absorption of carbon dioxide by plants. Unfortunately, deforestation in the world is in expanding, and the problem of greenhouses and rising temperatures worldwide contributes to the growing problem. The reduction of the Earth's green mantle, especially in Brazil and Argentina in order to increase livestock is one of the causes of the increase in the amount of CO₂ in the air.

Possibilities of improving CO₂ intake by polyethyleneamines were investigated, using zinc-silicate supports [1], as well as other methods [2-4]. It is known that different models have been tested in order to absorb carbon dioxide, either in industrial plants or directly exposed to air (since carbon dioxide is obtained as a by-product of many industrial plants, its release greatly affects environmental pollution). A special problem is the exhaust gases from cars, where carbon dioxide and water vapor are obtained as a product in the process of fuel combustion. All the carbon dioxide that goes into the atmosphere as a result of human activities has a great impact on environmental pollution, creating a greenhouse effect and raising the average temperature, which directly affects the climate. At least its partial elimination from industrial plants would already significantly

[#] corresponding author: n.djordjevic@itnms.ac.rs

reduce its concentration and slow down the process of environmental pollution. It is of great importance to monitor the level of carbon dioxide in the air, whether it is natural disasters that contribute to disturbances of the atmosphere, water and soil, or human impact through heavy and automotive industry and life in big cities [5-14].

EXPERIMENTAL

In order to investigate the possibility of improving the absorption capacity of sodium carbonate, Na_2CO_3 was mechanochemically activated in a high-energy mill with torsion springs and ring working elements "KHD HUMBOLDT WEDAGAG". The mill consists of a housing in which there is a mechanism with a horizontally placed working vessel. The working vessel of the mill has a cylindrical shape of small height and is located on a specially constructed bearing with a cap. Under the working vessel of the mill, which has a vibrating oscillatory movement, there is a drive mechanism with an elastic shaft. The eccentric flywheel and torsion springs convert the circular motion of the elastic shaft into the vibrating oscillatory motion of the working vessel of the mill. The working vessel has two massive annular working elements of different diameters, with a total weight of 3 kg, which occupy one third of the working volume of the mill. The lid of the working vessel of the mill has a felt seal around the perimeter. The base of the working vessel of the mill is placed horizontally on the body of the mill.

The volume of the working vessel of the mill is 2 dm^3 , and the mass of material that can be activated under optimal conditions is 200 g. Engine power is 0.8 kW. The device works discontinuously in an air atmosphere. Intense vibrating movement of the working vessel of the mill with massive rings, leads to heating of the vessel to a temperature of $80 \text{ }^\circ\text{C}$.

A sample of Na_2CO_3 , weighing 50 g, was activated by mechanochemical procedure for 1, 3, 5, 7, 14 and 28 minutes. The activated samples are then disposed of in order to absorb carbon dioxide. Exposure to activated sodium carbonate depends on the current needs of the environment in terms of carbon dioxide absorption (industrial plant, laboratory conditions, closed or open system, atmospheric conditions, already existing equipment using CO_2 absorbent). The standing time of the samples was from 1 to 85 days. The temperature at which the samples were deposited was room temperature. As a function of the activation time in the mechanochemical reactor, the residence time of the sample after activation and the atmosphere in which the sample is located (carbon dioxide content in the atmosphere), it is necessary to monitor changes in CO_2 in the atmosphere and activated sodium carbonate using different methods. was followed by the BET method. Crystallographic tests of activated Na_2CO_3 were performed. X-ray diffraction of polycrystalline samples was performed on a PHILIPS PW-1700, an automated diffractometer with a copper tube, which operates at 40 kV and 35 mA. The device is equipped with a graphite monochromator and a proportional counter filled with xenon. Shooting angle (2Θ) of $4\text{-}15 \text{ }^\circ$.

The bond energy values represented in sodium carbonate are as follows [9]:

- a) Na - O (364 kJ/mol)
- b) C - O (1076.4 kJ/mol)
- c) C = O (532.2 kJ/mol)

The decomposition temperature of sodium carbonate is $851 \text{ }^\circ\text{C}$. Sodium carbonate has a monoclinic crystal lattice ($a = 8.907$; $b = 5.239$; $c = 6.043$), specific gravity 2500

kg/m³. The chemical composition of sodium carbonate according to the catalog MERCK index 11.8541, and the content of Na₂CO₃ was 99.5%. A chemical analysis was performed on a representative sample, which is in full agreement with MERCK's characterization.

RESULTS AND DISCUSSION

The increase in the specific surface area of Na₂CO₃ determined by the BET method as a function of the time of mechanochemical activation is shown in Figure 1. The highest degree of fragmentation and increase of free surface area was achieved in the first 40 minutes of activation, from 6.8 m²/g of inactivated sample to 8.25 m²/g. In the period from 40 to 100 minutes of activation, the free surface area continues to increase slightly, so that the free surface area of ground sodium carbonate for 28 minutes is 8.6 m²/g. An increase in the free surface area of activated sodium carbonate indicates the possibility of a significant increase in the adsorption capacity of CO₂ from the air.

Mechanochemically activated Na₂CO₃ samples were submitted for X-ray diffraction analysis. The samples were isolated from the outside atmosphere, so that no additional influence on the already activated samples could occur. The aim of this analysis was to establish how the structure of sodium carbonate behaved as a function of the grinding time in the vibro mill. Table 1 shows the intensities of diffraction peaks of activated Na₂CO₃ depending on the activation time. Figure 2 shows the diffractograms of Na₂CO₃ activated for 1-21 min in a vibro mill.

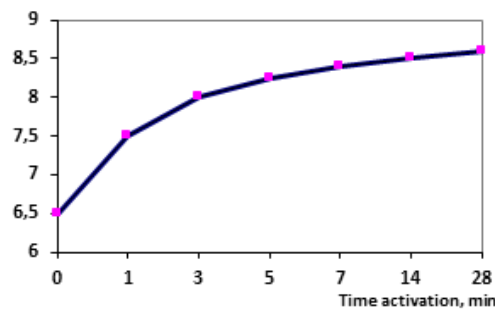


Figure 1 Change of specific surface of Na₂CO₃ as a function of time of mechanochemical activation by BET method

Table 1 Values of the intensity of diffraction maxima at a certain diffraction angle as a function of the activation time of Na₂CO₃ samples

Diffraction angle, 2 Θ	Peak intensities I (cts) depending on the activation time, min					
	1 min	3 min	5 min	7 min	14 min	28 min
30	350	193	199	276	177	193
34.165	146	128	125	142	106	108
35.225	222	166	164	228	144	154
37.965	310	196	174	228	146	156
40	154	194	83	106	72	86
Middle value 35.471	236	155	149	196	158	139

As a function of the time of activation of sodium carbonate, the crystal lattice is disturbed at all diffraction angles and the free surface of the activated material is increased. During the first five minutes of activation, there is a sharp decrease in the value of the intensity of diffraction maxima. Between the fifth and seventh minutes of grinding, the values of the maximum intensity increase, also at all diffraction angles. The increase in the intensity of diffraction maxima can be explained by the fact that after five minutes of grinding, after the collapse of the crystal structure, the mechanical energy supplied to the system allows a certain recrystallization of the existing system, the partial arrangement of the destroyed structure. After the fifth minute, the intensities decrease again until the fourteenth minute of grinding, after which the change in the intensity of the maximum has a steady flow with a slight tendency to increase in function from the time of grinding. This stationary flow of the curve can be explained by the assumption that after the collapse of the newly formed structure, after 14 minutes of grinding, no changes in the structure of the activated sample occur. It can also be concluded that by further extending the grinding time after 28 minutes, no further change in the structure of the activated material would be achieved.

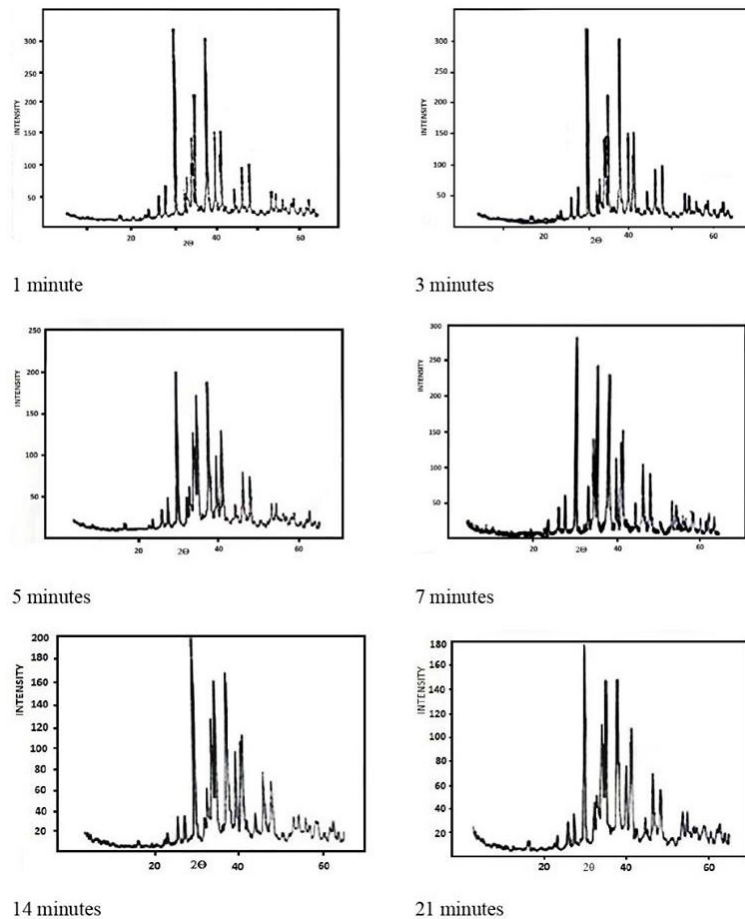


Figure 2 Diffractograms of Na_2CO_3 activated 1-21 min in a vibro mill

The results of the BET method after activation indicate the fact that due to grinding there was a significant increase in the free surface area of the activated sodium carbonate powder. As sodium carbonate is a known sorbent of carbon dioxide from the air, increasing the free surface area of the activated powder significantly increases the possibility of CO₂ sorption.

Comparing the results of the diffractograms of the activated samples in relation to the inactivated sample, it can be noticed that the grinding of sodium carbonate led to a disturbance of the crystal structure. In order to monitor the change in the intensity of diffraction maxima as a function of the activation time, five characteristic peaks at certain values of diffraction angles were selected from the data given with the diffractograms. Based on the analysis, it can be concluded that during 28 minutes of activation there is a sudden and significant decrease in the value of the intensity of diffraction maxima, ie the collapse of the crystal structure, at all angles of diffraction. This is due to the fact that the invested mechanical energy is spent on the comminution of existing grains of sodium carbonate, and then leads to the collapse of the internal structure of Na₂CO₃ crystals.

Based on the results, it can be seen that during the first five minutes of activation, there is a sharp decrease in the value of the intensity of diffraction maxima, the collapse of the crystal structure, at all angles of diffraction. This is a consequence of the fact that the invested mechanical energy is spent on crushing the existing grains of sodium carbonate, and then it leads to the destruction of the internal structure of the Na₂CO₃ crystal. Between the fifth and seventh minutes of grinding, the values of the maximum intensity increase at all diffraction angles. The increase in the intensity of diffraction maxima can be explained by the fact that after five minutes of grinding, after the collapse of the crystal structure, the mechanical energy supplied to the system allows a certain recrystallization of the existing system, partial arrangement of the destroyed structure.

As sodium carbonate is an effective carbon dioxide absorption agent, based on the attached research results, it can be concluded that mechanochemical activation can significantly contribute to an additional increase in the absorption capacity of sodium carbonate. In the next course of experiments, it is important to determine the increase in the degree of CO₂ absorption on sodium carbonate as a function of activation time, by monitoring the change in sample mass during relaxation in atmospheres with increased CO₂ concentration and humidity, and spectrophotometric analysis of activated samples after relaxation time.

CONCLUSION

Based on the results of the BET method of samples of sodium carbonate activated from 1 to 28 minutes, it can be concluded that grinding the samples leads to a significant increase in the free surface area of activated material, which increases the possibility of adsorption and absorption (sorption by surface area and volume) of CO₂. From the results obtained by diffractometric analysis, a significant destruction of the crystal lattice of the ground sample is observed, which enables not only the sorption of CO₂, but also the hemisorption of gas on the activated sample. The results of further tests will be presented in the next paper. Increasing the sorption capacity of CO₂ on sodium carbonate opens up great possibilities for its application in environmental protection, especially in industrial conditions.

ACKNOWLEDGEMENT

The authors are grateful to the Ministry of Education, Science and Technological Development of the Republic of Serbia for their support in the research whose results are presented in the paper (contract 451-03-68 / 2020-14 / 200023).

REFERENCES

1. Kuwahara, Y., Kang, D.Y., Copeland, J.R., Brunelli, N.A., Didas, S.A., Bollini, P., Sievers, C., Kamegawa, T., Yamashita, H., Jones, C.W. (2012) Diamine-functionalized metal-organic framework: exceptionally high CO₂ capacities from ambient air and flue gas, ultrafast CO₂ uptake rate, and adsorption mechanism. *J. Am. Chem. Soc.*, 134, 10757–10760.
2. Borhani, T.N.G., Azarpour, A., Akbari, V., Alwi, S.R.W., Manan, Z.A. (2015) Effective Capture of Carbon Dioxide Using Hydrated Sodium Carbonate Powders. *Int. J. Greenh. Gas Control.*, 41, 142–162.
3. Choi, S., Drese, J.H., Jones, C.W. (2009) Adsorbent Materials for Carbon Dioxide Capture from Large Anthropogenic Point Sources. *Chem. Sus. Chem.*, 2, 796–854.
4. Xu, Y., Zhou, Y., Liu, J., Sun, L. (2017) Effective Capture of Carbon Dioxide Using Hydrated Sodium Carbonate Powders. *J. Energy Chem.*, 26, 1026–1029.
5. Gilman, P., Benjamin, J. (1983) Mechanical alloying of brittle materials, *Ann. Rev. Materials. Sci. Paolo Alto*, 13, 279.
6. Obradović, N., Fahrenholtz, W.G., Filipović, S., Corlett, C., Đorđević, P., Rogan, J., Vulić, P.J., Buljak, V., Pavlović, V. (2019) Characterization of MgAl₂O₄ Sintered Ceramics. *Sci. Sinter.*, 51, 363-376.
7. Labus, N., Obradović, N., Srećković, T., Mitić, V., Ristić, M.M. (2005) Influence of mechanical activation on zinc metatitanate synthesis. *Sci. Sint.* 37, 115-122.
8. Filipovic, S., Obradovic, N., Petrovic, V. (2009) Influence of mechanical activation on structural and electrical properties of sintered MgTiO₃ ceramics. *Science of Sintering*, vol. 41, no. 2, 117-123.
9. Đorđević, N. G., Obradović, N. N., Filipović, S. Ž. (2011) Kinetika mehanohemijske sinteze barijum-titanata. *Tehnika-Novi materijali* 20:3 367-371.
10. Đorđević, N., Obradović, N., Filipović, S., Živojinović, J., Mltrić, M., Marković, S. (2012) Influence of Mechanical Activation on the Constituents of the MgO-Al₂O₃-SiO₂-TiO₂ System. *Tehnika–Novi materijali* 21 3, 329-333.
11. Liang, Y. (2003) Carbon dioxide capture from flue gas using regenerable sodium-based sorbents, Carbon dioxide capture from flue gas using regenerable sodium-based sorbents. Master`s Thesis, Louisiana State University.
12. Dusek, M., Chapuis, G., Meyer, M., Petricek, V. (2003) Thermodynamic Aspect of Sodium Carbonate Mechanical Transformations under Different Environment. *Acta Crystallog B* 59 (3), 337–352.
13. Li, J., Hitch, M. (2017) Ultra-fine grinding and mechanical activation of mine waste rock using a planetary mill for mineral carbonation. *International Journal of Mineral Processing* 158:18-26.
14. Boldyrev, V. V. (1986) Mechanochemistry of inorganic solids. *Proceedings of Indian National Science Academy*, 52, A, 1 400-417.