

**Proceedings of the 7th Slovenian-Serbian-Croatian
Symposium on Zeolites**
**Proceedings of the 7th Serbian-Croatian-Slovenian
Symposium on Zeolites**
**Proceedings of the 7th Croatian-Slovenian-Serbian
Symposium on Zeolites**

Abbreviated title:
Proc. Croat.-Slov.-Serb. Symp. Zeolites

ISSN 2584-3176

Publisher
Croatian Zeolite Association (CROZA)

Editors
Nataša Zabukovec Logar
Nevenka Rajić
Josip Bronić

Print
KOPIR BIRO BALEN, Zagreb
CROATIA

Copies
60

Zagreb, 2017.

PROCEEDINGS OF THE
7th SLOVENIAN-SERBIAN-CROATIAN
SYMPOZIUM ON ZEOLITES

May 25-27, 2017.
Ljubljana, Slovenia

Organizers

SLOVENIAN ZEOLITE ASSOCIATION
SERBIAN ZEOLITE ASSOCIATION
CROATIAN ZEOLITE ASSOCIATION

Under the auspices of
Federation of European Zeolite Associations (FEZA)

All articles in this Proceedings were reviewed.

Organizing committee:

Prof. **Nataša Zabukovec Logar**, National Institute of Chemistry, Ljubljana and University of Nova Gorica, Slovenia, chair

Prof. **Nataša Novak Tušar**, National Institute of Chemistry, Ljubljana and University of Nova Gorica, Slovenia, co-chair

Dr. **Tomaž Čendak**, National Institute of Chemistry, Ljubljana, Slovenia, secretary

Prof. **Vesna Rakić**, University of Belgrade, Faculty of Agriculture, Serbia

Prof. **Nevenka Rajić**, University of Belgrade, Faculty of Technology and Metallurgy, Serbia

Dr. **Josip Bronić**, Ruđer Bošković Institute, Zagreb, Croatia

Dr. **Karolina Maduna Valkaj**, University of Zagreb, Faculty of Chemical Engineering and Technology, Croatia

Scientific committee:

Prof. **Gregor Mali**, National Institute of Chemistry, Ljubljana, Slovenia

Prof. **Anton Meden**, University of Ljubljana, Faculty of Chemistry and Chemical Technology, Slovenia

Prof. **Venčeslav Kaučič**, National Institute of Chemistry, Ljubljana, Slovenia

Prof. **Djordje Stojaković**, University of Belgrade, Faculty of Technology and Metallurgy, Serbia

Prof. **Vladimir Simić**, University of Belgrade, Faculty of Mining and Geology, Serbia

Prof. **Nediljka Vukojević Medvidović**, University of Split, Faculty of Chemistry and Technology, Croatia

Prof. **Jasna Hrenović**, University of Zagreb, Faculty of Science, Croatia

Dr. **Sanja Bosnar**, Ruđer Bošković Institute, Zagreb, Croatia

Dr. **Tatjana Antonić Jelić**, Ruđer Bošković Institute, Zagreb, Croatia

LEACHING BEHAVIOUR OF NATURAL “LOW COST” SORBENTS SATURATED WITH ZINC AND COPPER

Marin Ugrina¹, Melita Petrić¹, Marija Marković², Aleksandra Daković², Nediljka Vukojević Medvidović¹, Marina Trgo¹, Ivona Nuić¹, Marija Mihajlović²

¹Faculty of Chemistry and Technology, University of Split, Ruđera Boškovića 35, 21000 Split, Croatia

²Institute for Technology of Nuclear and Other Mineral Raw Materials, Franče d' Epre 86, 11000 Belgrade, Serbia

E-mail: nvukojev@ktf-split.hr

ABSTRACT

The leachability of zinc and copper from natural *low-cost* sorbents through saturation and leaching study was examined in order to investigate their possible application as materials for permeable reactive barrier (PRB). Examined *low cost* sorbents were natural and iron-modified zeolite (IMZ), apatite, concentrated apatite, kaolin and raw bentonite. The highest saturation ability towards zinc and copper was detected with raw bentonite and IMZ. Leaching of zinc and copper has been confirmed from all saturated sorbents at pH=2.94, while at pH=6.46 was not detected. This indicates that among investigated sorbents, raw bentonite and IMZ are the most promising materials for removal of zinc and copper in PRB.

Keywords: *low-cost* sorbent, leachability, permeable reactive barrier, zinc, copper

INTRODUCTION

Natural *low-cost* sorbents such as zeolite, clay and apatite have great potential as materials for *in situ* remediation of contaminated groundwater using permeable reactive barrier (PRB). However, retention strength of sorbed ions in saturated sorbents is very important in application of these materials as PRB. Therefore, the present study is focused on investigation of leaching properties of the natural and iron-modified zeolite (NZ and IMZ), apatite, concentrated apatite, kaolin and raw bentonite saturated with copper and zinc.

EXPERIMENTAL

Materials: Natural zeolite (NZ) was supplied from Zlatokop deposit in Vranjska Banja (Serbia), bentonite was originated from Šipovo deposit (Bosnia), apatite from ore deposit Lisina, near Bosilegrad (Serbia), while kaolin was obtained from plant for production of quartz sand in Rgotina (Serbia). Iron-modified zeolite (IMZ) and concentrate apatite was prepared from original zeolite and apatite, respectively, according to well-known procedures.^[1,2]

Saturation experiment: The saturation of sorbents with zinc and copper was examined from simulated wastewater with the similar initial metal concentrations, $c_o(\text{Zn}) = 10.107 \text{ mmol/l}$ and $c_o(\text{Cu}) = 10.083 \text{ mmol/l}$, at S/L ratio 10 g/L, during 48 hours at room temperature, using batch mode. As our previous experiment showed that copper in system of Cu-IMZ is precipitated, thus the pH values of initial copper solutions in this system were adjusted at pH=2.52.^[3] During all experiments, pH values were recorded, and concentrations of heavy metals were determined before and after experiment.

Leaching experiment: The leaching experiment included evaluation of metal retained by the saturated sorbents in ultrapure water with adjusted pH values at 2.94 and 6.46, at S/L ratio 10

g/L, during 24 hours at room temperature. During experiments, pH values of solutions were recorded, and concentrations of heavy metals after experiment were determined.

RESULTS AND DISCUSSION

Saturation experiment

Time-dependent saturation experiment is monitored by pH values of solutions in Fig. 1, while amounts of loaded heavy metals on different sorbents are given in Fig. 2.

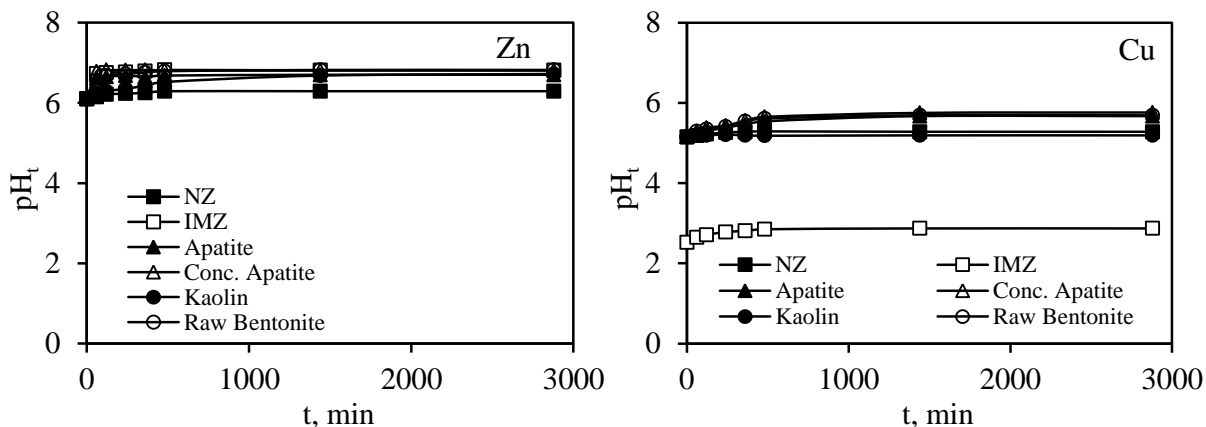


Fig. 1. pH values of solution during saturation experiment.

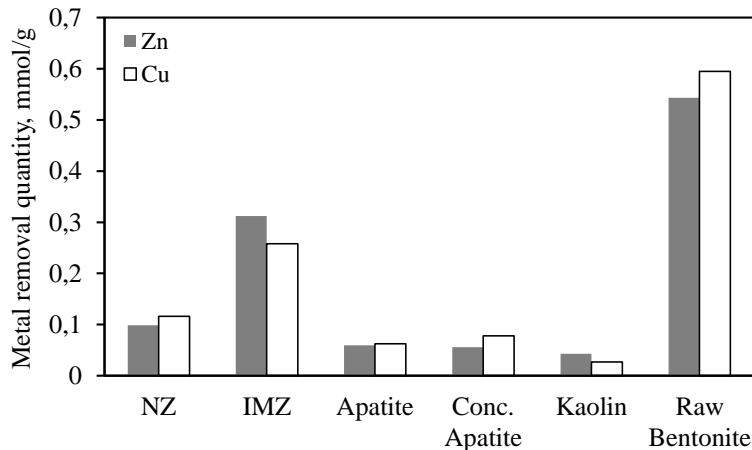


Fig. 2. Amount of loaded zinc and copper on different sorbents.

Slightly increase of pH of solutions in all examined systems were evident, which is connected with decrease of metal concentration in solution and diminishing influence of hydrolyse reaction of metal ions. Almost similar amounts of zinc and copper were sorbed onto investigated sorbents, confirming their similar affinities.

The highest sorbed amount of heavy metals was detected with raw bentonite, followed by IMZ, while lower amount was sorbed by NZ, conc. apatite and apatite. The lowest amount of sorbed heavy metals was observed for kaolin.

Leaching experiment

Time-dependent leaching experiment was followed by measuring the pH values of solutions (Figs. 3 and 4), while leaching of zinc and copper from metal-saturated sorbents in ultrapure water solution of pH=2.94 and 6.46, is given in Fig. 5.

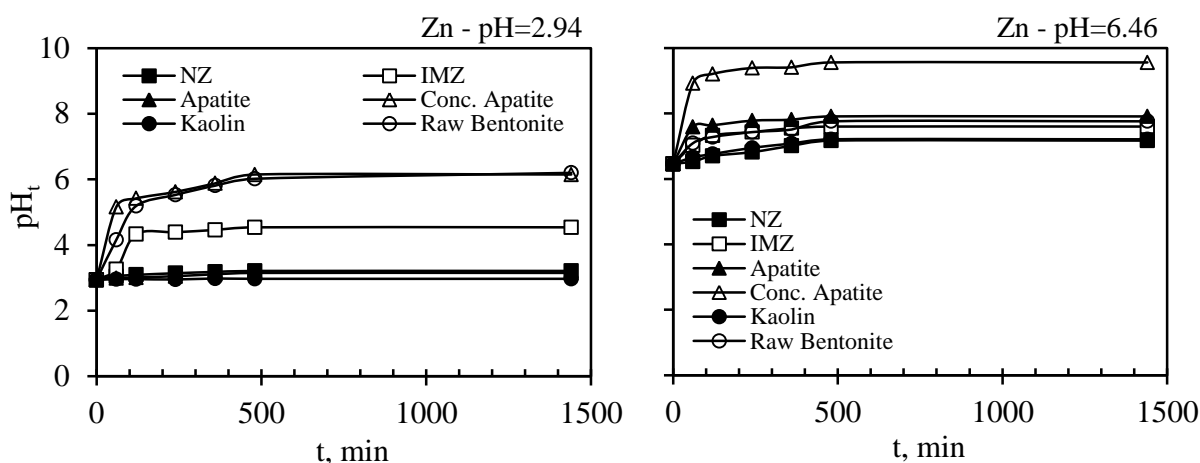


Fig. 3. pH values of solution during Zn leaching experiment from solution of pH=2.94 and 6.46.

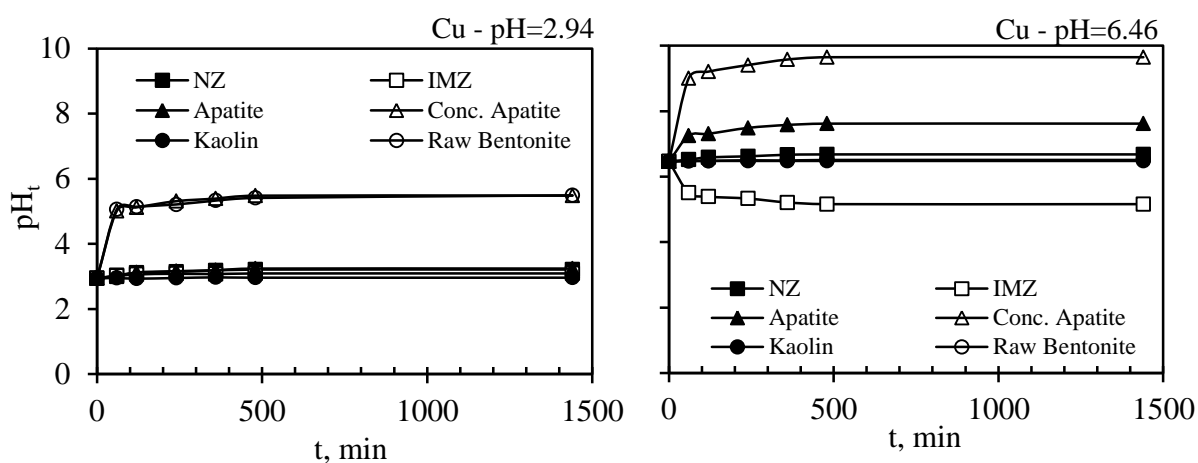


Fig. 4. pH values of solution during Zn leaching experiment from solution of pH=2.94 and 6.46.

Fig. 3 shows that at $pH_0=2.94$, slight increase of pH values is evident in system of metal ions with IMZ, conc. apatite and raw bentonite. At $pH_0=6.46$, slight increase is evident for all examined system, and is most pronounced for IMZ.

At $pH_0=6.46$, leaching of zinc and copper is not recorded. At $pH_0=2.94$ leaching of Zn and Cu is evident for all examined sorbents except leaching of Zn from kaolin. Lower pH values encourage competition of H^+ ions, thus leaching of Zn and Cu was more pronounced. Absence

of zinc leaching from kaolin is a consequence of lower amount of sorbed Zn during saturation experiment.

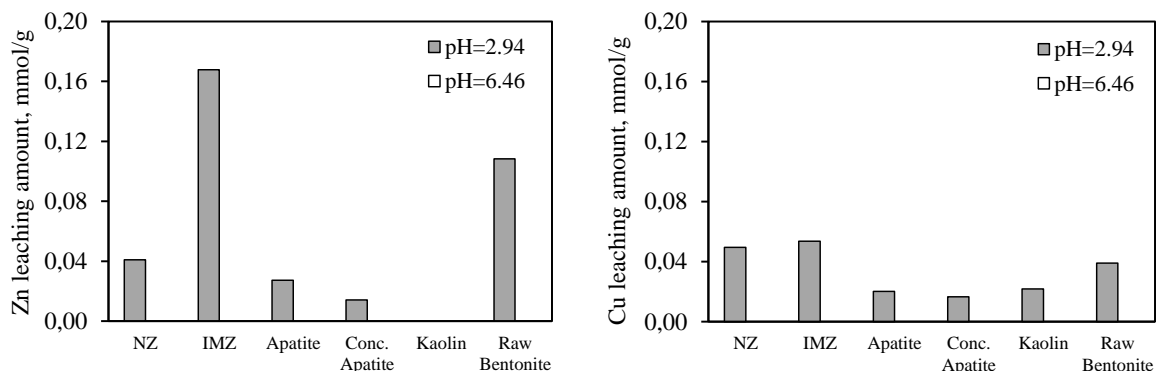


Fig. 5. Leaching amount of zinc and copper from saturated sorbents in solution of pH=2.94 and 6.46.

CONCLUSION

Saturation and leaching of zinc and copper at $pH_0=6.07$ for all examined sorbents are performed in slightly acidic to neutral solution, indicating their suitability for *in situ* application. Due to presence of higher amounts of H^+ ions at $pH=2.94$, leaching of Zn and Cu is recorded from all saturated sorbents. Among examined sorbents, raw bentonite and IMZ showed the highest sorption of zinc and copper confirming their potential as materials in PBR. However, further experiments should be focused on the investigation of hydraulic properties, satisfactory mechanical properties for safe performance, in order to ensure a smooth flow of contaminated groundwater through the barrier without disturbing the natural flow.

Acknowledgement

These experiments were performed under bilateral Croatian-Serbian project “Low-cost sorbents as potential materials for *in situ* remediation of heavy-metal contaminated groundwater”.

REFERENCES

- [1] M. Ugrina, N. Vukojević Medvidović, A. Daković, *Desalin. Water Treat.* **2015**, 53, 3557–3569.
- [2] A. F. Taggart, *Handbook of Mineral Dressing, Ore and Industrial Minerals*, John Wiley & Sons, Ltd, New York, London, **1960**.
- [3] M. Ugrina, N. Vukojević Medvidović, M. Trgo, I. Nuić, in *Proc. Eurasia Waste Manag. Symp. 2016* (Ed.: M. Sinan Bilgili), Istanbul, **2016**, pp. 832–839.