

MME SEE

CONGRESS 2023

5th Metallurgical & Materials Engineering
Congress of South-East Europe
Trebinje, Bosnia and Herzegovina
7-10th June 2023

CONGRESS PROCEEDINGS

MME SEE

C O N G R E S S 2 0 2 3

**5th Metallurgical & Materials Engineering
Congress of South-East Europe
Trebinje, Bosnia and Herzegovina
7-10th June 2023**

**CONGRESS
PROCEEDINGS**

Main Organizer

The Association of Metallurgical Engineers of Serbia

Co-organizers

Institute for Technology of Nuclear and Other Mineral Raw Materials in Belgrade, Serbia;

The Faculty of Technology and Metallurgy at the University of Belgrade, Serbia;

The Faculty of Technology at the University of Banja Luka, Bosnia and Herzegovina;

The Faculty of Metallurgy at the University of Zagreb in Sisak, Croatia;

The Faculty of Natural Sciences and Engineering at the University of Ljubljana, Slovenia;

The Faculty of metallurgy and technology at the University of Podgorica, Montenegro.

CONGRESS PROCEEDINGS - MME SEE 2023

5th Metallurgical & Materials Engineering Congress of South-East Europe

Editors:

Dr. Miroslav Sokić,

Institute for Technology of Nuclear and Other Mineral Raw Materials

Dr. Branislav Marković

Institute for Technology of Nuclear and Other Mineral Raw Materials

prof. Dr. Vaso Manojlović

Faculty of Technology and Metallurgy, University of Belgrade

Technical editor:

M. Sc. Gvozden Jovanović

Institute for Technology of Nuclear and Other Mineral Raw Materials

Published and printed by:

Association of Metallurgical Engineers of Serbia (AMES)

Kneza Miloša 9/IV,

11000 Belgrade

Serbia

For the publisher:

AMES president Dr. Miroslav Sokić

Circulation:

120 copies

ISBN 978-86-87183-32-2

GOLD SPONSOR



SILVER SPONSOR



LEADING TECHNICALLY
QUALIFIED EXPERTS

vacuum
cryotechnics
electron microscopy



ИНЖЕЊЕРСКА
КОМОРА
СРБИЈЕ



Град
Требиње

Scientific Committee

- *Miroslav Sokić, Serbia, president*
- *Marija Korać, Serbia, vice president*
- *Sanja Martinović, Serbia, vice president*
- Aleksandra Daković, Serbia
- Ana Kostov, Serbia
- Bernd Friedrich, Germany
- Borislav Malinović, Bosnia and Herzegovina
- Boštjan Markoli, Slovenia
- Branislav Marković, Serbia
- Corby Anderson, USA
- Dragomir Glišić, Serbia
- Duško Minić, Serbia
- Efthymios Balomenos, Greece
- Hakan Atapek, Turkey
- Hasan Avdušinović, Bosnia and Herzegovina
- Jarmila Trpčevska, Slovakia
- Jasna Stajić-Trošić, Serbia
- Jovana Ružić, Serbia
- Karlo Raić, Serbia
- Kemal Delijić, Montenegro
- Lijun Zhang, China
- Ljubica Radović, Serbia
- Martin Debelak, Slovenia
- Mile Đurđević, Austria
- Miljana Popović, Serbia
- Mirjam Jan Blažić, Slovenia
- Miroslav Ignjatović, Serbia
- Nada Štrbac, Serbia
- Natalija Dolić, Croatia
- Nebojša Tadić, Montenegro
- Nenad Radović, Serbia
- Pasquale Daniele Cavaliere, Italy
- Petar Uskoković, Serbia
- Rossita Paunova, Bulgaria
- Srećko Manasijević, Serbia
- Srećko Stopić, Germany
- Tatjana Volkov-Husović, Serbia
- Vaso Manojlović, Serbia
- Veljko Đokić, Serbia
- Vesna Maksimović, Serbia
- Vladan Čosović, Serbia
- Zdenka Zovko-Brodarac, Croatia
- Željko Kamberović, Serbia

Organizing Committee

- *Branislav Marković, Serbia, president*
- *Vaso Manojlović, Serbia, vice president*
- Aleksandar Jovanović, Serbia
- Gvozden Jovanović, Serbia
- Milena Obradović, Serbia
- Mladen Bugarčić, Serbia
- Nela Vujović, Serbia
- Nikola Kanas, Serbia
- Stefan Dikić, Serbia

Reviewer Committee

- **Aleksandar Jovanović, Serbia**
- **Aleksandar Savić, Serbia**
- **Aleksandra Daković, Serbia**
- **Blažo Lalević, Serbia**
- **Bojan Međo, Serbia**
- **Boštjan Makroli, Slovenia**
- **Branislav Marković, Serbia**
- **Branko Matović, Serbia**
- **Dragana Živojnović, Serbia**
- **Dragana Radovanović, Serbia**
- **Dragomir Glišić, Serbia**
- **Dušica Pešević, Bosnia and Herzegovina**
- **Gvozden Jovanović, Serbia**
- **Ivana Cvijović-Alagić, Serbia**
- **Jelena Avdalović, Serbia**
- **Jelena Lović, Serbia**
- **Jovana Perendija, Serbia**
- **Karlo Raić, Serbia**
- **Kemal Delijić, Montenegro**
- **Ksenija Nešić, Serbia**
- **Maja Đolić, Serbia**
- **Maja Obradović, Serbia**
- **Marija Ercegović, Serbia**
- **Marija Korać, Serbia**
- **Marina Jovanović, Bosnia and Herzegovina**
- **Milica Pošarac Marković, Serbia**
- **Milisav Ranitović, Serbia**
- **Miljana Popović, Serbia**
- **Miroslav Sokić, Serbia**
- **Mladen Bugarčić, Serbia**
- **Nebojša Nikolić, Serbia**
- **Nenad Radović, Serbia**
- **Rada Petrović, Serbia**
- **Silvana Dimitrijević, Serbia**
- **Srđan Matijašević, Serbia**
- **Srećko Stopić, Germany**
- **Stevan Dimitrijević, Serbia**
- **Suzana Filipović, Serbia**
- **Tatjana Volkov-Husović, Serbia**
- **Vaso Manojlović, Serbia**
- **Vladan Čosović, Serbia**
- **Zoran Anđić, Serbia**
- **Zoran Stević, Serbia**
- **Željko Kamberović, Serbia**

PREFACE

On behalf of the Scientific and Organizing Committee, it is a great honor and pleasure to wish all the participants a warm welcome to the Fifth Metallurgical & Materials Engineering Congress of South-East Europe (MME SEE 2023) which is being held in Trebinje, Bosnia and Hercegovina, 07 - 10 June 2023.

The MME SEE 2023 is a biannual meeting of scientists, professionals, and specialists working in the fields of metallurgical and materials engineering. The aim of the Congress is to present current research results related to processing/structure/property relationships, advances in processing, characterization, and applications of modern materials. Congress encompasses a wide range of related topics and presents the current views from both academia and industry: Future of metals/materials industry in South-East European countries; Raw materials; New industrial achievements, developments and trends in metals/materials; Ferrous and nonferrous metals production; Metal forming, casting, refractories and powder metallurgy; New and advanced ceramics, polymers, and composites; Characterization and structure of materials; Recycling and waste minimization; Corrosion, coating, and protection of materials; Process control and modeling; Nanotechnology; Sustainable development; Welding; Environmental protection; Education; Accreditation & certification.

The editors hope that Congress will stimulate new ideas and improve knowledge in the field of metallurgical and materials engineering. The Congress has been organized by the Association of Metallurgical Engineers of Serbia, with the co-organization of the Institute for Technology of Nuclear and Other Mineral Raw Materials, Belgrade, Serbia, Faculty of Technology and Metallurgy, University of Belgrade, Serbia, Faculty of Technology, University of Banja Luka, Bosnia and Herzegovina; the Faculty of Metallurgy, University of Zagreb, Sisak, Croatia; the Faculty of Natural Sciences and Engineering, University of Ljubljana, Slovenia; and the Faculty of Metallurgy and technology, University of Podgorica, Montenegro.

Financial support from the Ministry of Science, Technological Development and Innovation of the Republic of Serbia to researchers from Serbia for attending the congress is gratefully acknowledged. The support of the sponsors and their willingness to cooperate have been of great importance for the success of MME SEE 2023. The Organizing Committee would like to extend their appreciation and gratitude to all sponsors and friends of the conference for their donations and support.

We would like to thank all the authors who have contributed to this book of abstracts and also the members of the scientific and organizing committees, reviewers, speakers, chairpersons, and all the conference participants for their support of MME SEE 2023. Sincere thanks to all the people who have contributed to the successful organization of MME SEE 2023.

On behalf of the 5th MME SEE Scientific and Organizing Committee

Miroslav Sokić, PhD

Table of Contents

Raw materials	1
<i>Vladimir Malbašić, Aleksandar Vasić</i> PRODUCTION AND PERSPECTIVES OF FOR LJUBIJA IRON ORES USE	3
<i>Marija Marković, Aleksandra Daković, Danijela Smiljanić, Milena Obradović, Milica Ožegović</i> BENTONITE CLAYS AS AFLATOXIN B1 ADSORBENTS	12
<i>Milica Vidak Vasić, Lidija Radovanović, Zagorka Radojević</i> RAW KAOLINITIC-ILLITIC CLAYS FOR THE PRODUCTION OF REFRACTORY CERAMICS ...	17
<i>Vladimir Jovanović, Dejan Todorović, Branislav Ivošević, Dragan Radulović, Mladen Bugarčić, Sonja Milićević</i> THE ADVANTAGES OF USING PELLETIZED GYPSUM COMPARED TO POWDERED GYPSUM.....	23
New industrial achievements, developments, and trends in metals/materials.....	29
<i>Srdan Stanković, Stefanie Hetz, Axel Schippers</i> PERSPECTIVES OF LATERITE BIOHYDROMETALLURGY	31
<i>Dragana Randelović, Gvozden Jovanović, Branislav Marković, Miroslav Sokić</i> REE EXTRACTION FROM HYPERACCUMULATING PLANTS: CHALLENGES AND PROSPECTS	37
<i>Grozdanka Bogdanović, Sanja Petrović</i> A NOVEL APPROACH TO COPPER LEACHING FROM CHALCOPYRITE WITH SULPHURIC ACID SOLUTIONS.....	44
<i>Sanja Jevtić, Vaso Manojlović, Milisav Ranitović, Nataša Gajić, Marija Štulović, Željko Kamberović</i> JAROSITE FROM ZINC HYDROMETALLURGY: THERMODYNAMIC AND KINETIC APPROACH	49
<i>Nenad Milosavljević, Tamara Ristić, Goran Jevtić, Mijajlo Jauković</i> ANALYSIS OF EFFECTIVNESS OF BOTTOM STIRRING AFTER THE MODERNIZATION ON BASIC OXYGEN FURNACE NO.2 IN HBIS SERBIA GROUP	56
Ferrous and nonferrous metals production	63
<i>Alexander Birich, Bernd Friedrich</i> GREEN GOLD PRODUCTION FROM PRIMARY AND SECONDARY RESOURCES	65
<i>Mile Đurđević, Srećko Manasijević</i> DETERMINATION OF OPTIMAL MODIFIER LEVEL FOR EUTECTIC SILICON PHASE IN HYPOEUTECTIC $AlSi_7Mg_{0.3}Cu_{0.5}$ CAST ALLOY.....	73
<i>Miloš Marković, Darija Đorđević, Vaso Manojlović, Aleksandar Vasić, Željko Kamberović</i> THE EFFECT OF THE PLASTIC TO COKE RATIO ON THE MOST CRITICAL PROCESS PARAMETERS IN A BLAST FURNACE.....	84
Metal forming, casting, refractories, and powder metallurgy	91
<i>Radomir Radiša, Srećko Manasijević, Nedeljko Dučić, Aleksandar Jovičić</i> CIRCULAR ECONOMY AND DIGITALIZATION IN CAST PRODUCTION	93

<i>Jelena Stašić, Milan Trtica, Jovana Ružić, Marko Simić, Andrijana Žekić, Dušan Božić</i> SURFACE EFFECTS INDUCED BY SHORT-PULSED LASERS ON PM-SYNTHESIZED CuCrZr ALLOY	98
<i>Marko Simić, Jovana Ružić, Jelena Erčić, Dušan Božić, Željko Radovanović, Jelena Stašić</i> INFLUENCE OF THE MILLING TIME ON THE STRUCTURAL PARAMETERS OF Cu-Zr-B ALLOYS	105
New and advanced ceramics, polymers, and composites	111
<i>Malia Athirah Badruddin, Mohd Sabri Mohd Ghazali, Muhamad Syaizwadi Shaifudin, Abdul Mu'iz Aniq Aiman Mohd Suhaimi, Wan Mohamad Ikhmal Wan Mohamad Kamaruzzaman, Nursabrina Amirah Mohd Nasir, Nusaibah Yusof, Chen Soo Kien</i> EFFECT OF DIFFERENT CaSiO ₃ CONTENTS ON THE MICROSTRUCTURE AND ELECTRICAL PERFORMANCE OF ZnO-BASED VARISTOR CERAMICS	113
<i>Wan Mohamad Ikhmal Wan Mohamad Kamaruzzaman, Muhamad Syaizwadi Shaifudin, Nursabrina Amirah Mohd Nasir, Nur Aiman Syaifiq Mohd Hamidi, Nusaibah Yusof, Azila Adnan, Lee Oon Jew, Wan Mohd Norsani Wan Nik, Mohd Sabri Mohd Ghazali</i> ANTICORROSIVE IMPROVEMENTS OF WATERBORNE POLYURETHANE COATINGS USING EGGHELLS BIOWASTE FOR MILD STEEL IN ARTIFICIAL SEAWATER.....	118
<i>Danina Krajišnik, Snežana Uskoković-Marković, Aleksandra Daković, Danijela Smiljanić, Maja Kozarski, Vesna Lazić</i> PREPARATION AND CHARACTERIZATION OF CHITOSAN-CLAY COMPOSITES AS POTENTIAL DRUG CARRIERS	123
<i>Muhamad Syaizwadi Shaifudin, Mohd Sabri Mohd Ghazali, Wan Mohamad Ikhmal Wan Mohamad Kamaruzzaman, Wan Rafizah Wan Abdullah, Lee Oon Jew</i> MICROSTRUCTURE AND ELECTRICAL PERFORMANCE OF BARIUM TITANATE DOPED ZINC OXIDE VARISTOR CERAMICS VIA MODIFIED CITRATE-GEL METHOD	128
Characterization and structure of materials.....	135
<i>Boštjan Markoli, Iztok Naglič, Blaž Leskovar, Adam Zaky, Žan Kresnik, Andrej Resnik</i> SPECIAL COPPER ALLOYS FOR MOULDS IN PRODUCTION OF HIGH-END GLASS PRODUCTS	136
<i>Iztok Naglič, Blaž Leskovar, Adam Zaky, Boštjan Markoli, Jovica Stojanović, Željko Kamberović</i> QUASICRYSTALS IN AL-MN-BASED ALLOYS CONTAINING COPPER, CALCIUM AND STRONTIUM.....	142
<i>Adam Zaky, Blaž Leskovar, Iztok Naglič, Boštjan Markoli</i> OPTIMISATION OF AN Al-Mn ALLOY REINFORCED WITH QUASICRYSTALS.....	147
<i>Gordana Marković, Vaso Manojlović, Miroslav Sokić, Jovana Ružić, Dušan Milojkov, Aleksandra Patarić</i> PREDICTING THE MODULUS OF ELASTICITY OF BIOCOMPATIBLE TITANIUM ALLOYS USING MACHINE LEARNING	154
<i>Tatjana Volkov-Husović, Sanja Martinović, Ana Ali, Milica Vlahović</i> CAVITATION EROSION RESISTANCE OF SOME ENGINEERING MATERIALS	159
<i>Sanja Martinović, Ana Alil, Aleksandar Savić, Dragomir Glišić, Dragana Živojinović, Tatjana Volkov-Husović</i> PRINCIPAL COMPONENT ANALYSIS OF MORPHOLOGICAL DESCRIPTORS FOR ASSESSMENT OF SURFACE DEFECTS INDUCED BY EXTREME CONDITIONS.....	164
<i>Jovana Ružić, Marko Simić, Dušan Božić, Nikolay Stoimenov, Stanislav Goshev, Jelena Stašić</i> STUDY OF THE CHANGES IN MECHANICAL PROPERTIES OF THE COPPER-ZIRCONIUM ALLOYS INFLUENCED BY MINOR BORON ADDITION	171

<i>Nadira Bušatlić, Ilhan Bušatlić, Dženana Smajić-Terzić</i> GEOPOLYMERS BASED ON FLY ASH FROM THE STANARI THERMAL POWER PLANT	177
<i>Ljubiša Balanović, Dajana Milkić, Dragan Manasijević,</i> <i>Ivana Marković, Milan Gorgievski, Uroš Stamenković, Kristina Božinović</i> MICROSTRUCTURAL AND THERMAL CHARACTERIZATION OF THE Bi–In–Sn TERNARY ALLOYS	184
<i>Ljubica Radović, Fernando Carrasco López, Igor Radisavljević, Nenad Radović</i> DISTRIBUTION OF ALLOYING ELEMENTS IN FRICTION STIR WELDED AA2024-T351 ALLOY	191
<i>Dragana Mihajlović, Marko Rakin, Đorđe Veljović, Bojan Međo, Veljko Đokić</i> ADVANCEMENT OF BIOCOMPATIBILITY AND MECHANICAL SURFACE CHARACTERISTICS OF THE Ti-13Nb-13Zr ALLOY USING ELECTROCHEMICAL ANODIZATION	198
<i>Natalija Dolić, Zdenka Zovko Brodarac, Franjo Kozina</i> INFLUENCE OF HOMOGENIZATION ON CHEMICAL PROPERTIES OF ALUMINUM ALLOY EN AW-5083	204
<i>Dragan Manasijević, Ljubiša Balanović, Ivana Marković, Milan Gorgievski,</i> <i>Uroš Stamenković, Kristina Božinović, Duško Minić, Milena Premović Zečević</i> MICROSTRUCTURE AND THERMAL CONDUCTIVITY OF THE Ag–Bi–Sn TERNARY ALLOYS	211
<i>Marija Mihailović, Aleksandra Patarić, Snežana Aksentijević, Branka Jordović</i> MICROSTRUCTURE DEVELOPMENT DURING HEAT TREATMENT OF HIGH CHROMIUM WHITE CAST IRON	216
<i>Aleksandra Patarić, Gordana Marković, Nataša Đorđević, Slavica Mihajlović, Marija Mihailović</i> MICROSTRUCTURE ASSESSMENT OF Co ALLOY INTENDED FOR DENTISTRY	221
<i>Maja Kokunešoski, Aleksandra Šaponjić, Zvezdana Baščarević,</i> <i>Ivan Jovanović, Jelena Filipović Tričković, Ana Valenta Šobot</i> PRELIMINARY CYTOTOXICITY TESTING OF NEWLY SYNTHESISED SBA-15 MATERIAL... 226	226
<i>Jelena Nikolić, Vladimir Topalović, Marija Došić,</i> <i>Veljko Savić, Milena Obradović, Srđan Matijašević, Snežana Grujić</i> DISSOLUTION OF POLYPHOSPHATE GLASS: IMPACT OF pH ON DIFFUSION COEFFICIENTS OF MODIFYING CATIONS AT LOW TEMPERATURES	231
<i>Tatjana Šoštarić, Stefan Kolašinac, Zorica Lopičić,</i> <i>Anja Antanasković, Vladimir Adamović, Jelena Avdalović, Mladen Bugarčić</i> CHARACTERIZATION OF RAW PEACH STONES AND ITS BIOCHAR BY SEM, FTIR AND RAMAN SPECTROSCOPY	237
<i>Aleksandar Đorđević, Milena Zečević, Duško Minić</i> EFFECT OF CHEMICAL COMPOSITION ON THE MICROSTRUCTURE, HARDNESS, AND ELECTRICAL CONDUCTIVITY OF THE TERNARY Bi-Cu-Ge SYSTEM.....	242
Recycling and waste minimization	249
<i>Zdenka Zovko Brodarac, Franjo Kozina, Davor Stanić, Martin Folta</i> QUALITY ASSESSMENT OF THE AlSi ₉ Cu ₃ (Fe) ALLOY WITH REGARD TO RECYCLING RATIO	251
<i>Sonja Smiljanić, Uroš Hribar, Matjaž Spraitzer, Jakob König</i> CRYSTALLIZATION CONTROL IN FOAM GLASS PREPARATION FROM CONTAINER GLASS WASTE	257

<i>Uroš Stojaković, Aleksandar Jovanović, Ivana Mikavica, Branislav Marković, Vladimir Pavićević</i> DIRECTIONS AND CHALLENGES OF THE CIRCULAR ECONOMY: MOVEMENT OF MUNICIPAL SOLID WASTE IN CITY OF PARAČIN	263
<i>Silvana Dimitrijević, Stevan Dimitrijević, Aleksandra Ivanović, Marija Korać, Milisav Ranitović</i> COMPARATION OF CORROSION AND MECHANICAL PROPERTIES OF COMMERCIAL AND RECYCLED 6060 AND 6082 ALUMINIUM ALLOYS	269
Corrosion, coating, and protection of materials	277
<i>Aleksandra Ivanović, Silvana Dimitrijević, Stevan Dimitrijević, Renata Kovačević</i> DEALLOYING OF PdNi5 ALLOY IN 1.0M NITRIC ACID.....	279
<i>Marija Korać, Stevan Dimitrijević, Kemal Deljić, Silvana Dimitrijević, Željko Kamberović</i> INFLUENCE OF ZINC ADDITION ON ANTI-TARNISH SILVER ALLOYS IN FOUR DIFFERENT SYSTEMS.....	286
<i>Miljana Popović, Ana Alil, Bojan Gligorijević, Endre Romhanji</i> INFLUENCE OF COLD ROLLING AND ANNEALING ON THE MECHANICAL AND CORROSION PROPERTIES OF AN AA5182 Al-Mg ALLOY.....	291
Process control and modeling	299
<i>Milana Zarić, Mirjana Kijevčanin, Ivona Radović</i> INFLUENCE OF FUNCTIONAL GROUPS ON THERMODYNAMIC PROPERTIES OF BINARY MIXTURES	301
<i>Gvozden Jovanović, Vaso Manojlović, Miroslav Sokić, Alen Delić, Milorad Gavrilovski</i> INFLUENCE OF MOLD PREHEATING ON RAILWAY ALUMINOTHERMIC WELDING CASTING SIMULATION.....	307
Sustainable development	315
<i>Branimir Grgur</i> CHALLENGES IN ENERGY STORAGE	317
<i>Dušan Milojkov, Miroslav Sokić, Angelina Mitrović, Danijela Smiljanić, Jelena Petrović, Marija Simić, Vukosava Živković-Radovanović</i> DEVELOPMENT OF SUSTAINABLE METHOD FOR METAL RECOVERY FROM OLD FLOTATION TAILINGS (MAJDANPEK, SERBIA) USING <i>Aspergillus niger</i> FUNGUS	325
Welding.....	331
<i>Stefan Dikić, Mihajlo Arandjelović, Simon Sedmak, Radomir Jovičić, Dragomir Glišić</i> EFFECTS OF MULTIPLE WELDING DEFECTS ON MECHANICAL PROPERTIES OF WELDED JOINT	333
<i>Nebojša Tadić, Mitar Mišović, Žarko Radović, Ratka Petrović</i> CHARACTERIZATION OF FRICTION STIR WELDING JOINTS IN 7075-T6 ALLOY PLATES...	339
Environmental protection.....	345
<i>Milica Stojković, Sofija Dedić, Maja Đolić, Mirjana Čujić, Vladimir Pavićević, Mirjana Ristić, Aleksandra Perić-Grujić,</i> THE OPTIMIZATION OF METALS AND METALLOIDS EXTRACTION FROM FLY ASH	347
<i>Aleksandar Jovanović, Mladen Bugarčić, Marija Stevanović, Miroslav Sokić, Aleksandar Marinković</i> SEQUENCING BATCH REACTOR SYSTEMS FOR THE TREATMENT OF WASTEWATER.....	353

<i>Marija Simić, Jelena Petrović, Marija Ercegović, Marija Koprivica, Jelena Dimitrijević, Aleksandar Jovanović, Dušan Milojkov</i> Mg/Fe-PYRO-HYDRO CHAR DERIVED FROM CORN COB AS EFFECTIVE ADSORBENT OF LEAD REMOVAL FROM AQUEOUS SOLUTIONS	359
<i>Janko Živanić, Mladen Bugarčić, Anja Antanasković, Zorica Lopičić, Miroslav Sokić, Aleksandar Jovanović, Milan Milivojević</i> THE ADSORPTION OF ARSENIC(V) IONS FROM AQUEOUS SOLUTIONS BY COMPOSITE OF NATURAL POLYMER AND METAL OXIDE	365
<i>Danijela Smiljanić, Aleksandra Daković, Milena Obradović, Marija Marković, Milica Ožegović, Milena Pantić, Danina Krajišnik</i> CLAY-CHITOSAN-SURFACTANT COMPOSITES AS EFFICIENT ADSORBENTS OF ZEARALENONE	371
<i>Nela Vujović, Vesna Alivojvodić, Miroslav Sokić, Gvozden Jovanović, Branislav Marković, Željko Kamberović</i> INNOVATIVE INDUSTRIAL SYMBIOSIS APPROACH FOR ACIDIC MINE DRAINAGE NEUTRALIZATION	377
<i>Jovana Bošnjaković, Nataša Knežević, Aleksandar Marinković, Srećko Manasijević, Andrija Savić, Milena Milošević</i> REMOVAL OF MESOTRIONE BY HETEROGENEOUS PHOTOCATALYTIC TREATMENT USING UV-VIS LAMP AS LIGHT SOURCE	383
<i>Nataša Knežević, Jovana Bošnjaković, Marija Vuksanović, Jovana Milanović, Ljiljana Janković-Mandić, Adela Egelja, Aleksandar Marinković</i> TESTING OF THE ADSORPTION-DEGRADATION CAPACITY OF CRYSTAL VIOLET DYE WITH OXIDIZED COTTON LINTERS	388
<i>Katarina Sokić, Jelena Dikić, Đorđe Veljović, Jovana Đokić, Zoran Anđić, Sanja Jevtić</i> MECHANOCHEMICAL SYNTHESIS AND CHARACTERIZATION OF THE ADSORBENTS BASED ON NATURAL ZEOLITE AND HYDROXYAPATITE	395
<i>Borislav Malinović, Anđela Bojić, Draženko Bjelić, Tijana Đuričić</i> NICKEL RECOVERY FROM STATIC RINSING IN THE ELECTROPLATING PROCESS	401
Sensors	409
<i>Jelena Vujančević, Špela Trafela, Neža Sodnik, Zoran Samardžija, Kristina Žagar Soderžnik</i> ELECTROCHEMICAL SENSORS FOR DETECTION OF BISPHENOLS	411
<i>Abhilash Krishnamurthy, Špela Trafela, Kristina Žagar Soderžnik</i> DETECTION AND SENSING OF BENZENEDIOLS USING MODIFIED SCREEN-PRINTED ELECTRODES	415
AUTOR INDEX	420

MICROSTRUCTURE ASSESSMENT OF Co ALLOY INTENDED FOR DENTISTRY

Aleksandra Patarić¹, Gordana Marković¹, Nataša Đorđević¹, Slavica Mihajlović¹, Marija Mihailović²

e-mail: a.patatic@itmms.ac.rs

1-Institute for Technology of Nuclear and other Mineral Raw Materials, Franchet d'Eperey St.86, 11000 Belgrade, Serbia

2-University of Belgrade - Institute of Chemistry, Technology and Metallurgy - National Institute of the Republic of Serbia, Njegoševa 12, Belgrade, Serbia

Cobalt–chromium–molybdenum (CoCrMo) alloys are known for medical use due to their biocompatibility, corrosion and wear resistance. The chemical and phase composition, as well as microstructure of the alloy directly affect the mechanical properties. In this investigation, CoCrMo alloy samples were obtained by vacuum precise casting. The procedure of melting and casting process as well as their parameters are given. Molds fabricated of copper, gray iron, steel, ceramics and graphite were used during the casting process. In this way, the cooling rate influence on the obtained microstructure was examined. Besides, different casting temperatures (1400°C, 1450°C and 1500°C) were applied for each kind of mold. After metallographic preparation, the microstructure was examined on the cross section of samples by optical microscopy. The obtained results show that by increasing the cooling rate, the microstructure of samples become finer and more homogeneous.

Keywords: CoCrMo alloy, vacuum precise casting, cooling rate

Introduction

Co-Cr-Mo alloys are distinguished by their high strength, biocompatibility, non-corrosiveness, and exceptional wear resistance [1, 2]. These alloys exhibit high fluidity and low viscosity at elevated temperatures, which allows for the casting of complex shapes [3]. These properties make them well-suited for use in dentistry for the manufacture of various dental components, including prostheses, bridges, dental crowns, and orthodontic appliances. Additionally, their resistance to tarnishing also makes them ideal for dental applications [4, 5]. Being in the aggressive environment of the oral cavity, Co-Cr-Mo alloys must be biocompatible [6]. Cobalt, chromium, and molybdenum are microelements in the human body, and these alloys are recognized as hypoallergenic [2]. They exhibit excellent corrosion resistance, owing to the formation of a passivating layer that inhibits the release of metal ions into the oral cavity [2, 7].

The microstructural characteristics of a material have a profound effect on its mechanical properties, thus defining its suitability for a given application [8]. A heterogeneous and coarse-grained microstructure usually results in low strength and increased brittleness, while a fine-grained, uniform morphology is a good indicator of superior strength. The final obtained structure largely depends on the processing temperature and cooling rate. Elevated processing temperatures are more likely to yield a homogeneous and coarse-grained structure, with a higher density of dislocations, compared to lower cooling temperatures [9]. Rapid cooling leads to the formation of fine crystals, which contributes to increased strength and ductility [10]. Different molds have different coefficients of thermal conductivity, with higher values corresponding to faster cooling [11].

Materials and methods

Alloy was prepared from the following elements Co (99.99 wt.%), Cr (99%), Mn (99.9%), Mo (99.8%), Si (98%) by vacuum precise casting in a vacuum induction furnace. Cobalt chromium and manganese are integral components of alloys, while manganese and silicon are important for detoxification and cleaning of alloys during melting. Granulation of raw materials is 0.5-5 mm.

In order to prevent the oxidation of the alloy and to obtain its appropriate chemical composition, the

casting process was carried out in a vacuum induction furnace. Melting and casting process was performed under the vacuum of 0.04 mbar. Five different kinds of molds with dissimilar thermal conductivity coefficients were prepared for casting alloys, from the following materials: copper (386 W/m.K), gray iron (52.5 W/m.K), ceramic (1.38 W/m.K), steel (50 W/m.K) and graphite (4180 W/m.K) [12, 13, 14, 15]. The molds should be preheated to the temperature of about 1000 °C while the casting temperatures were in range of 1450-1550 °C. After melting, casting and cooling, five series of samples cast in five different molds were made. The microstructure of samples (cast in five different molds) was examined after the usual metallographic preparation. The samples were ground and polished. Polishing was carried out using alumina suspension (Al_2O_3) that was applied on a rotating self-adhesive disc. A mixture of potassium ferrocyanide, potassium hydroxide and water was used for samples etching. For the qualitative microstructure analysis the image analysis device Leica Q500MC was used.

Results and discussion

The characteristic microstructure appearance at the cross section of samples casted in five different molds is shown in Figures 1, 2, 3, 4 and 5. Sample 1 was cast in graphite-base mold, sample 2 in copper mold, sample 3 in gray iron mold, sample 4 in steel mold and sample 5 in ceramic mold.

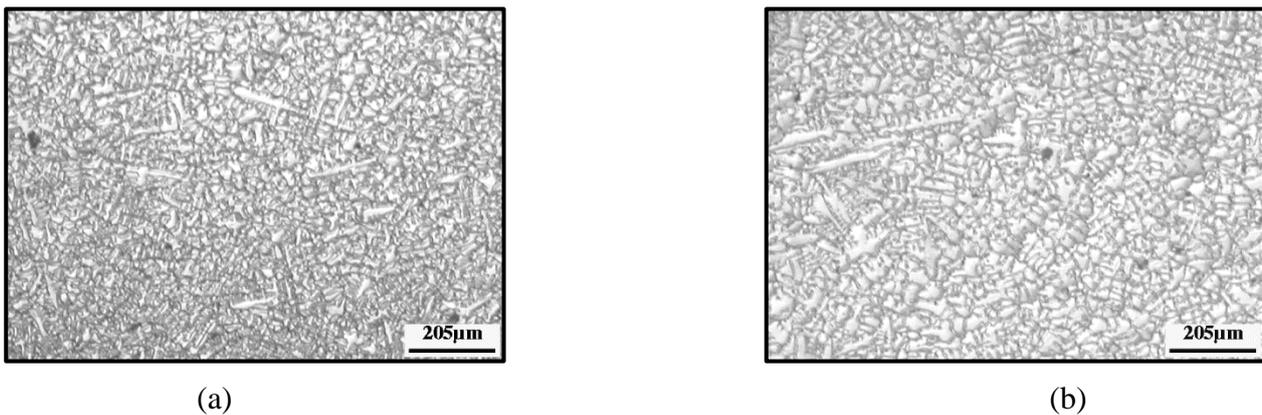


Figure 1 Microstructure of sample 1 cross section, (graphite-base mold), surface area (a) center (b)

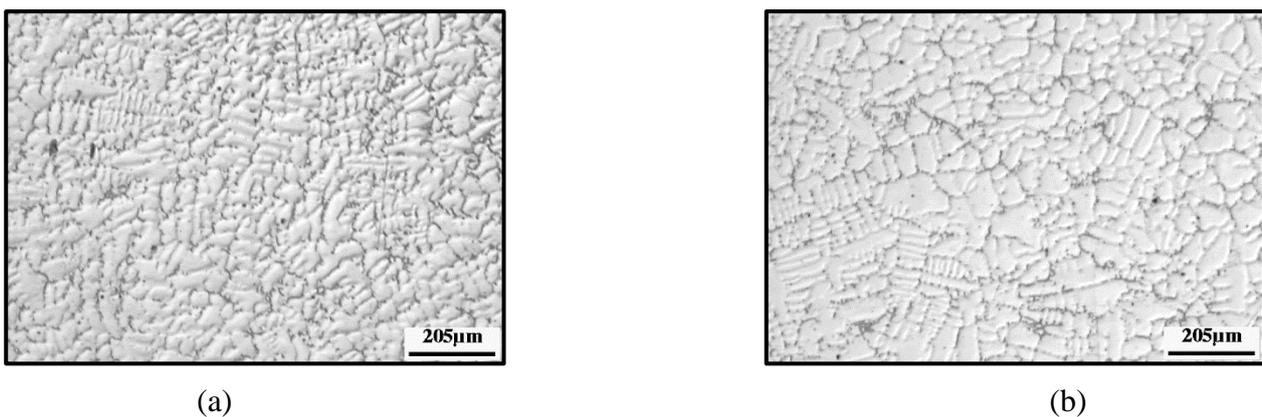


Figure 2 Microstructure of sample 2 cross section, (copper mold), surface area (a) center (b)

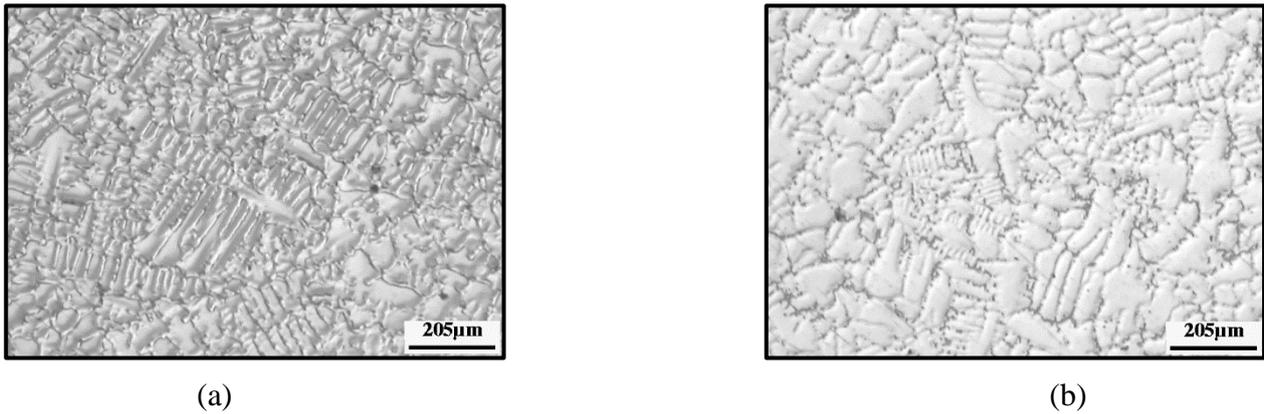


Figure 3 Microstructure of sample 3 cross section, (gray iron mold), surface area (a) center (b)

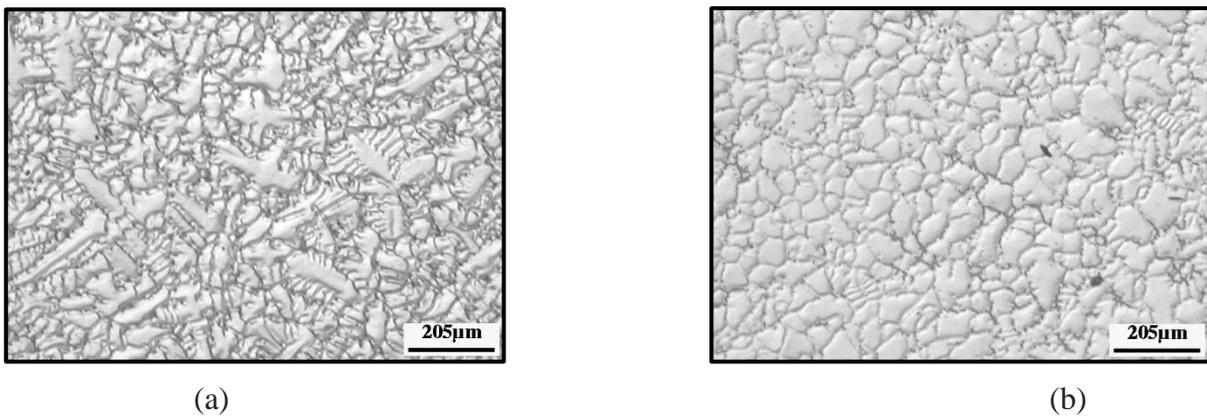


Figure 4 Microstructure of sample 4 cross section, (steel mold), surface area (a) center (b)

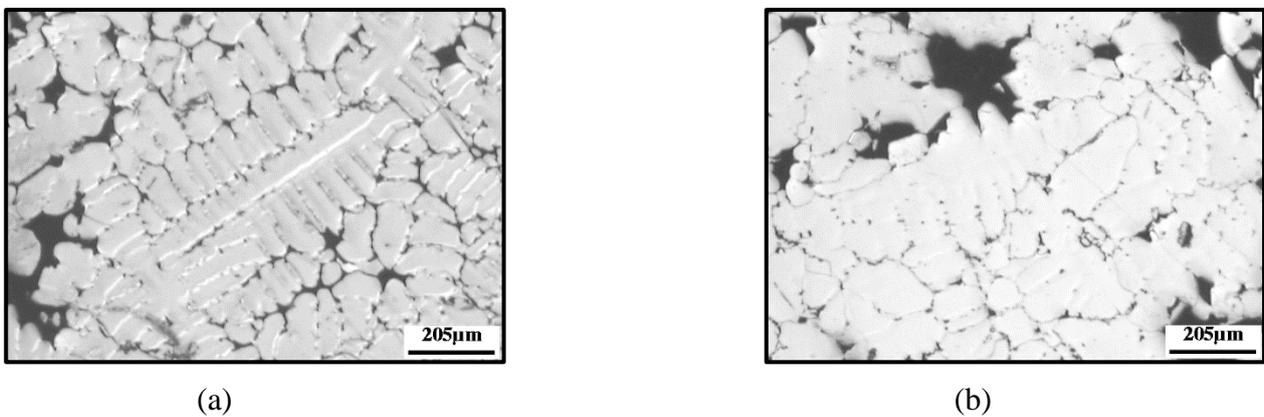


Figure 5 Microstructure of sample 5 cross section, (ceramic mold), surface area (a) center (b)

As it can be seen, the cellular/dendritic morphology is the result of Co segregation from the solid solution during the solidification process. However, the morphology of the samples differs from one another. This is a consequence of the different cooling rate, because each material (five kinds of molds) has various thermal conductivity coefficients. If the thermal conductivity coefficient is higher, the cooling rate is also higher. The finest and the most homogenous is microstructure of the sample 1 and 2, cast in graphite-base mold and copper mold, because of the high cooling rate. With cooling rate decrease, the microstructure became less fine and more dendritic (samples 3 and 4).

Due to the small difference in thermal conductivity coefficients, the microstructure of samples 3 and 4, does not differ significantly. Sample 5 has the roughest microstructure with pronounced dendrites and a lot of porosity, because of the lowest cooling rate.

In all samples, a slightly larger grain can be observed in the center compared to the surface area. This is also a consequence of the cooling rate decreasing from the surface area to the center of samples.

Conclusion

Results of microstructure assessment of the samples reveal a difference in the morphology, size and shape of the grains. The cooling rate directly affects the obtained microstructure of the alloy. The higher cooling rate results in a finer and more homogeneous microstructure, which is the case with the samples 1 and 2 cast in graphite base mold and copper mold. Some less fine and less homogeneous microstructure has samples 3 and 4 cast in gray iron mold and steel mold. The poorest microstructure with porosity appears, has sample 5 cast in ceramic mold. It is clear that the cooling rate directly affects the microstructure and that the appropriate structure can be achieved by properly choosing the material from which the mold is made. This is very important because the mechanical properties depend on the microstructure, which will be the subject of study in our following researches.

Acknowledgement

This work was supported by the Ministry of Science, Technological Development and Innovations, Grant No. 451-03-47/2023-01/200026 (IHTM) and Grant No.451-03-47/2023-01/200023 (ITNMS).

References

- [1] Ren, Zhe, Steven Eppell, Sunniva Collins, and Frank Ernst. "Co–Cr–Mo alloys: Improved wear resistance through low-temperature gas-phase nitro-carburization." *Surface and Coatings Technology* 378 (2019): 124943.
- [2] Łukaszczyk, A., and J. Augustyn-Pieniżek. "Corrosion resistance of Co-Cr-Mo alloy used in dentistry." *Archives of metallurgy and Materials* 60, no. 1 (2015): 523-528.
- [3] Liu, R., S. Q. Xi, S. Kapoor, and X. J. Wu. "Investigation of solidification behavior and associate microstructures of Co–Cr–W and Co–Cr–Mo alloy systems using DSC technique." *Journal of materials science* 45 (2010): 6225-6234.
- [4] Averyanova, Maria, Philippe Bertrand, and Benoît Verquin. "Manufacture of Co-Cr dental crowns and bridges by selective laser Melting technology: This paper presents the successful application of the selective laser melting technology in dental frameworks manufacturing from Co-Cr alloy using Phenix PM 100T Dental Machine over a production period of 14 months." *Virtual and Physical Prototyping* 6, no. 3 (2011): 179-185.
- [5] De Aguiar, S. R. M. M., M. Nicolai, M. Almeida, and A. Gomes. "Electrochemical behaviour of a cobalt–chromium–molybdenum dental alloy in artificial salivas." *Bio-medical materials and engineering* 25, no. 1 (2015): 53-66.
- [6] Giacchi, J. V., C. N. Morando, O. Fornaro, and H. A. Palacio. "Microstructural characterization of as-cast biocompatible Co–Cr–Mo alloys." *Materials characterization* 62, no. 1 (2011): 53-61.

- [7] Moslehifard, Elnaz, Tahereh Ghaffari, Samineh Mohammadian-Navid, Mina Ghafari-Nia, Amirali Farmani, and Farzad Nasirpouri. "Effect of chemical passivation on corrosion behavior and ion release of a commercial chromium-cobalt alloy." *Journal of Dental Research, Dental Clinics, Dental Prospects* 14, no. 3 (2020): 171.
- [8] Bakkaloğlu, Adem. "Effect of processing parameters on the microstructure and properties of an Nb microalloyed steel." *Materials letters* 56, no. 3 (2002): 200-209.
- [9] Ko, Kyung-Ho, Hyeon-Goo Kang, Yoon-Hyuk Huh, Chan-Jin Park, and Lee-Ra Cho. "Effects of heat treatment on the microstructure, residual stress, and mechanical properties of Co–Cr alloy fabricated by selective laser melting." *Journal of the Mechanical Behavior of Biomedical Materials* 126 (2022): 105051.
- [10] Zhuang, L. Z., and E. W. Langer. "Effects of cooling rate control during the solidification process on the microstructure and mechanical properties of cast Co-Cr-Mo alloy used for surgical implants." *Journal of materials science* 24 (1989): 381-388.
- [11] Ahmadein, M., Ammar H. Elsheikh, and Naser A. Alsaleh. "Modeling of cooling and heat conduction in permanent mold casting process." *Alexandria Engineering Journal* 61, no. 2 (2022): 1757-1768.
- [12] Fuchs, Hans U. *The dynamics of heat: a unified approach to thermodynamics and heat transfer*. New York, NY, USA:: Springer, 2010.
- [13] Fundições, Tupy. "Thermal conductivity of gray iron and compacted graphite iron used for cylinder heads." *Revista Matéria* 10, no. 2 (2005): 265-272.
- [14] Langenberg, E., E. Ferreiro-Vila, V. Leborán, A. O. Fumega, V. Pardo, and F. Rivadulla. "Analysis of the temperature dependence of the thermal conductivity of insulating single crystal oxides." *APL Materials* 4, no. 10 (2016): 104815.
- [15] Dong, Kaijun, Xiaobin Gu, Lihua Peng, Peng Liu, Shuai Jiang, and Liang Bian. "Recent advancements in typical mineral-encapsulated form-stable phase change materials for thermal energy storage." *Journal of Energy Storage* 52 (2022): 104931.