

9th Croatian-Slovenian-Serbian Symposium on Zeolites



PROCEEDINGS

Editors

Ivona Nuić

Matjaž Mazaj

Aleksandra Daković

Split, 2021

Proceedings of the 9th Croatian-Slovenian-Serbian
Symposium on Zeolites

Proceedings of the 9th Slovenian-Serbian-Croatian
Symposium on Zeolites

Proceedings of the 9th Serbian-Croatian-Slovenian
Symposium on Zeolites

Publisher

Croatian Zeolite Association (CROZA)

Editors

Ivona Nuić

Matjaž Mazaj

Aleksandra Daković

Split, 2021

PROCEEDINGS OF THE
9th CROATIAN-SLOVENIAN-SERBIAN
SYMPOSIUM ON ZEOLITES

September 23-25, 2021
Split, Croatia

Organizers
CROATIAN ZEOLITE ASSOCIATION
SLOVENIAN ZEOLITE ASSOCIATION
SERBIAN ZEOLITE ASSOCIATION

Under the auspices of
Federation of European Zeolite Association (FEZA)

All articles in the Proceedings were reviewed.

CONTENTS

<i>Plenary lecture: Opportunities in defects engineering and healing in zeolites</i>	1
Izabel C. Medeiros-Costa, Eddy Dib, Nikolai Nesterenko, Jean-Pierre Dath, Jean-Pierre Gilson, <u>Svetlana Mintova</u>	
<i>Invited lecture: Examining zeolitic imidazolate frameworks (ZIFs) for ethanol adsorption</i>	2
Ciara Byrne	
Synthesis and characterization of boron modified zeolite with MFI structure	6
<u>Sanja Bosnar</u> , Vladislav Rac, Ljiljana Damjanović-Vasilić, Vladimir Pavlović, Steva Lević, Josip Bronić, Vesna Rakić	
Green synthesis of ZIF-90 and its mixed metal analogues	10
<u>Aljaž Škrjanc</u> , Ciara Byrne, Matjaž Mazaj, Nataša Zabukovec Logar	
Effect of metal cations in FAU type zeolite on acid sites	14
<u>Glorija Medak</u> , Josip Bronić, Andreas Puškarić, Nina Popov	
Distribution of Al sites in SSZ-13 zeolites	18
Katarina Kopljar, Karen Janella Ardila Fierro, Andraž Krajnc, Matjaž Mazaj, <u>Ana Palčić</u>	
Fe and Ce exchanged ZSM-5 zeolites as electrocatalysts for ORR and OER reactions	22
Jadranka Milikić, Biljana Šljukić, Ivana Stojković Simatović, Ljiljana Damjanović-Vasilić, Srna Stojanović, <u>Vladislav Rac</u> , Vesna Rakić	
<i>Plenary lecture: Past and future of zeolite materials</i>	26
Valentin Valtchev	
<i>Invited lecture: The durability properties of concrete incorporating zeolitic tuff</i>	27
Zinoviy Blikharskyy, Khrystyna Sobol, <u>Taras Markiv</u> , Oksana Pozniak, Wojciech Franus	
Ni/ZSM-5 as efficient catalyst for the selective hydrogenation of levulinic acid to γ-valerolactone in vapor phase	31
<u>Hue-Tong Vu</u> , Andrii Kostyniuk, Petar Djinović, Miha Grilc, Blaž Likozar, Nataša Zabukovec Logar, Nataša Novak Tušar	
Photocatalysis of bisphenol A in aqueous solution by zeolite/titania composites	35
<u>Srna Stojanović</u> , Vladislav Rac, Vesna Rakić, Ljiljana Damjanović-Vasilić	
Photocatalytic removal of dyes from wastewater under solar lights by natural clinoptilolite from different regions	39
<u>Jelena Pavlović</u> , Andraž Šuligoj, Nevenka Rajić	
Composites of phillipsite-rich tuff and surfactant – their characterization and stability	43

<u>Danijela Smiljanić</u> , Aleksandra Daković, Milica Spasojević, Milena Obradović, Marija Marković, Alessio Langella, Bruno de Gennaro	
Removal of arsenic(III) oxyanions from wastewater using aminosilane-modified natural and synthetic zeolite	47
<u>Jelena Dimitrijević</u> , Jelena Petrović, Dragana Milošević, Jelena Dikić, Sanja Jevtić	
ZSM-5 as sorbent for removal of linuron from water	51
Ivana Mihajlović, Ali Hgeig, <u>Mladenka Novaković</u> , Nevena Živančev, Maja Petrović	
Silanol networks in zeolites investigated with solid-state NMR	55
<u>Eddy Dib</u> , Izabel C. Medeiros-Costa, Georgi Vayssilov, Hristiyan Aleksandrov, Svetlana Mintova	
Characterization of metal species in metal-modified hierarchical mordenite	59
<u>Ivana Landripet</u> , Marko Robić, Andreas Puškarić, Josip Bronić	
<i>Plenary lecture: Zeolite template carbon performances in catalytic and adsorption applications</i>	63
Girolamo Giordano	
<i>Invited lecture: The height of the Schottky barrier versus the photocatalytic activity of TiO₂+Au composites under visible-light illumination</i>	64
<u>Gregor Žerjav</u> , Albin Pintar	
The efficiency of natural clinoptilolite for ciprofloxacin removal from aqueous media	68
<u>Barbara Kalebić</u> , Jelena Pavlović, Jelena Dikić, Aleksander Rečnik, Nikola Škoro, Nevenka Rajić	
Does bacterial surface hydrophobicity level influence their immobilization onto natural zeolite?	72
<u>Jasna Hrenović</u> , Darko Tibljaš, Svjetlana Dekić Rozman, Tomislav Ivanković	
Natural zeolite as a tool for modelling bacterial biofilm development in static conditions	75
<u>Tomislav Ivanković</u> , Katarina Rotim, Jasna Hrenović	
Preparation and antibacterial activity of composites based on thymol/carvacrol and clinoptilolite	79
<u>Jelena Dikić</u> , Ivana Lukić, Jelena Pajnik, Jelena Pavlović, Jasna Hrenović, Nevenka Rajić	
Comparison of coagulation and electrocoagulation with addition of natural zeolite for treatment of biowaste compost leachate	83
<u>Nediljka Vukojević Medvidović</u> , Ladislav Vrsalović, Ivona Jukić, Ana-Maria Šunjić	
Analysis of Bohart-Adams model equations for description of adsorption in fixed bed-column	87
<u>Nediljka Vukojević Medvidović</u> , Sandra Svilović	

Equilibrium study of copper ions adsorption on the natural clinoptilolite-rich zeolitic tuff	91
<u>Mario Nikola Mužek</u> , Anđela Čović, Anita Bašić, Sandra Svilović	
Prediction of zeolite barrier capability in treatment of groundwater polluted by Pb, Cd and Zn	95
<u>Ivona Nuić</u> , Matea Šušnjara, Marina Trgo, Nediljka Vukojević Medvidović, Marin Ugrina	
<i>Plenary lecture: Zeolite surface passivation: “Core-shell” systems from synthesis to catalytic applications</i>	99
Massimo Migliori	
<i>Invited lecture: Environmental-friendly modified natural zeolites as sorbents for <i>in situ</i> remediation of mercury-contaminated soil in Idria region, Slovenia</i>	100
<u>Marin Ugrina</u> , Teja Čeru, Ivona Nuić, Marina Trgo, Aleksandra Daković	

REMOVAL OF ARSENIC(III) OXYANIONS FROM WASTEWATER USING AMINOSILANE-MODIFIED NATURAL AND SYNTHETIC ZEOLITE

Jelena Dimitrijević¹, Jelena Petrović¹, Dragana Milošević², Jelena Dikić³, Sanja Jevtić⁴

¹ Institute for Technology of Nuclear and Other Mineral Raw Materials, 86 Franchet d'Esperey St., 11000 Belgrade, Serbia

² Institute of Chemistry, Technology and Metallurgy, Centre for Materials and Metallurgy, Karnegijeva 4, Belgrade, Serbia

³ Innovation Centre of the Faculty of Technology and Metallurgy, University of Belgrade, Karnegijeva 4, Belgrade, Serbia

⁴ Faculty of Technology and Metallurgy, University of Belgrade, Karnegijeva 4, Belgrade, Serbia
E-mail: sanja@tmf.bg.ac.rs

ABSTRACT

Silanization of the natural and synthetic zeolites as well as their use as adsorbents for removing arsenic(III) oxyanions from wastewater are the topic of this paper. Two types of zeolite were used: natural zeolite-clinoptilolite from Zlatokop deposit, Vranjska Banja, Serbia, previously converted to H⁺-form and synthetic zeolite, mordenite. The modification was performed with solution (3-aminopropyl) triethoxysilane (APTES). The presence of APTES on the surface of zeolite was confirmed using TG/DSC and FTIR analysis. The results showed that natural aminosilane-modified zeolite has a higher adsorption capacity for arsenic(III) oxyanions compared to mordenite prepared in the same way. The kinetic data follow the Lagergren pseudo-second-order model. This model implies a chemical interaction between AsO₃³⁻ ions and functional groups on the silanized zeolite surface.

Key words: zeolite, aminosilane, modification, arsenic, wastewater.

INTRODUCTION

Into the environment arsenic comes from various sources, including industrial wastewater, the use of fertilizers and pesticides, the smelting of metal ores and the combustion of fossil fuels [1]. Due to its high toxicity even at low concentrations, it is considered one of the most undesirable metals, so its removal from wastewater is a major environmental challenge [1,2]. Zeolites are good adsorbents for the removal of different metals from aqueous solutions [3,4]. The adsorption mechanism is mainly based on an ion-exchange reaction between cations from zeolite lattice and metal ions from water solutions [5]. In order to improve the adsorption capacity of zeolites various organic compounds, such as amino-silanes are used. Amino-silanes are binding to the surface of the zeolite, whereby amino groups participate in the interaction with metal ions, thus improving the chemisorption's properties of the starting material. In this study, we performed a modification of clinoptilolite and mordenite with (3-aminopropyl) triethoxysilane (APTES) and examined their ability to remove As(III) from water solutions.

EXPERIMENTAL

Natural zeolite-clinoptilolite (Zlatokop, Serbia) and synthetic zeolite-mordenite (CZM20, SiO₂/Al₂O₃ molar ratio 20, Clariant) were chemically modified using (3-aminopropyl)triethoxysilane (APTES, 99%, Acros Organics). Before silanization, clinoptilolite was chemically treated and converted to H⁺-form according to the procedure described by Garcia-Basabe *et al.* [6] while mordenite preliminarily was calcined for 30 minutes at 550 °C in order to remove potentially present moisture. Silanization was performed in a balloon with a reflux condenser in an inert stream of nitrogen in the presence of toluene as a liquid medium. The silanization process was performed for 9 h with continuous stirring on a magnetic stirrer and on a constant temperature of 70 °C. The APTES was added in drops to the reaction mixture

during the whole time of stirring. After the silanization, ethanol was added in drops at 10 min intervals several times. After completion of the silanization process, the modified zeolites were centrifuged and washed to remove toluene from the zeolite surface. The zeolite samples were dried for 24 h at 70 °C. In the adsorption experiments, the liquid/solid phase ratio was 100:1. The initial concentration of As(III) solution was 10 mg As dm⁻³. The suspensions were stirred at room temperature for 24 h. After the selected time (0.25, 0.5, 1, 2, 4, 6 and 24 h) aliquots were taken. The suspensions were separated by filtration and the concentration of As(III) before and after adsorption were determined by Perkin Elmer PinAAcle 900T Atomic Absorption Spectrometer (AAS)- Mercury Hydride System (MHS).

Characterization. Powder X-ray diffraction analysis (PXRD) was used to check crystallinity of the H⁺-form of clinoptilolite after modification. PXRD patterns were recorded in the 2 Θ =5–40° at room temperature using an Ital Structure APD2000 diffractometer. APTES content were determined by thermogravimetric analysis using a SDT Q-600 simultaneous TG/DSC instrument (TA Instruments). Interactions of APTES with zeolite surface were studied by Fourier Transform Infrared (FTIR) spectroscopy in the range 4000–450 cm⁻¹ at room temperature using MB Bomem 100 Hartmann & Brown spectrometer. All samples were prepared by the KBr method.

RESULTS AND DISCUSSION

The PXRD analysis of the natural zeolite (Clin) and H⁺-form of this zeolite showed that the clinoptilolite lattice after modification was not affected (Fig. 1).

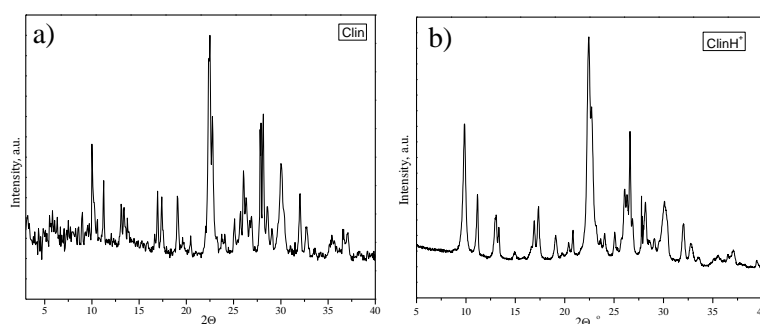


Figure 1. PXRD patterns of Clin (a) and ClinH⁺ (b).

The results of thermal analysis (TG/DSC) are shown in Fig. 2 and 3. The total weight loss at 800 °C for samples ClinH⁺ and ClinH⁺-APTES is 12.4 and 15.3 wt.%, respectively. This confirms that the organic component has bound to the zeolite surface. DSC-curve of ClinH⁺-APTES shows peak at 310 °C which is a consequence of the degradation of aminosilanes.

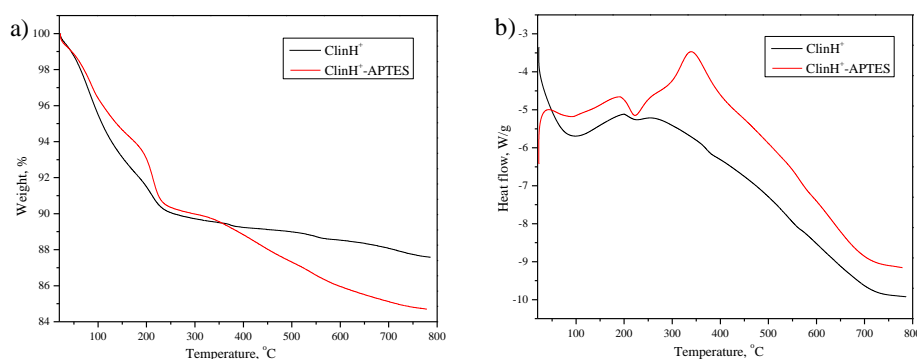


Figure 2. TG (a) and DSC (b) curves of ClinH⁺ and ClinH⁺-APTES.

As it can be seen from the Fig. 3, the TG curves of modernite shows that modified mordenite has a greater weight loss (15.4 wt.%) in comparison to the unmodified sample (12.5 wt.%) which confirms the presence of APTES. On the DSC curve of the modified sample a peak at about 320 °C can be observed which can be attributed to the organic component (Fig. 3b).

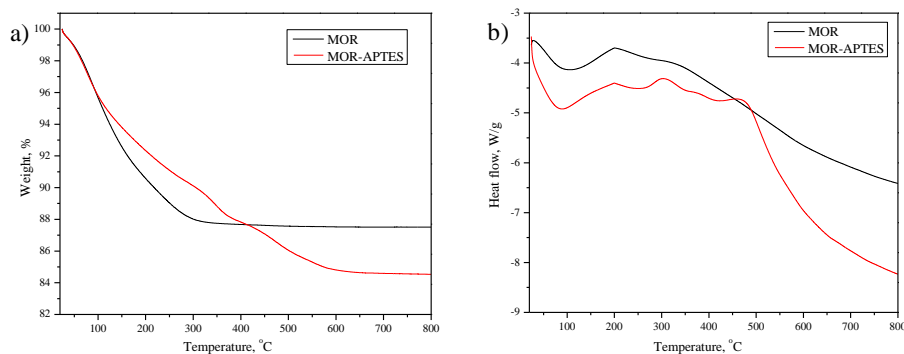


Figure 3. TG (a) and DSC (b) curves of MOR and MOR-APTES.

The FTIR spectra were used to analyse surface functionalities of ClinH⁺ and MOR, as well as the successfulness of their modification with APTES (ClinH⁺-APTES and MOR-APTES) (Fig. 4).

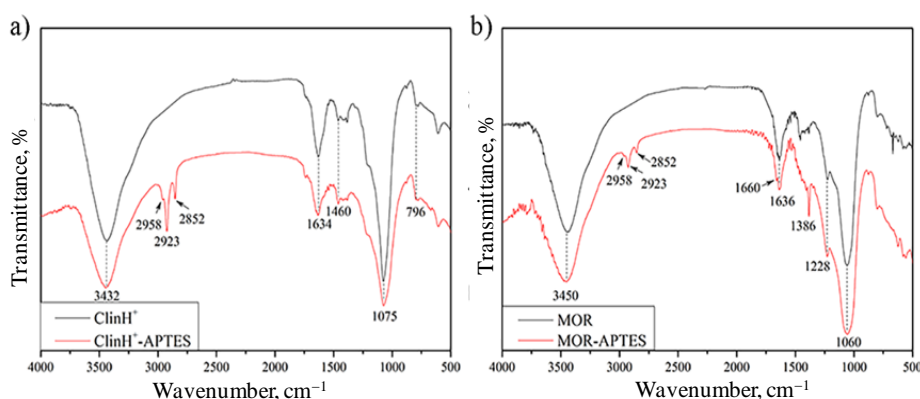


Figure 4. FTIR spectra of: (a) ClinH⁺ and ClinH⁺-APTES; (b) MOR and MOR-APTES.

FTIR spectra of all samples (Fig. 4) shows an intense band that occurs in the range between 3400-3500 cm⁻¹ assigned with -OH stretching vibrations of surface functional groups, while the peak at 1634 cm⁻¹ originates from -OH bending vibration, related with cations located in the structure of zeolite channels. The characteristic band at 1060-1075 cm⁻¹ corresponds to the asymmetric stretching vibration of internal Si-O and Al-O bonds in SiO₄ and AlO₄ tetrahedral groups. The band at 796 cm⁻¹ is assigned with the stretching vibration mode of O-Si-O and O-Al-O groups in the zeolite structure [7]. Besides the absorption bands of vibration frequencies of -OH, Si-O and Al-O groups, the appearance of new bands at spectra of silan-modified zeolites was observed and is associated with successful APTES modification. The peaks at 2958, 2923 and 2852 cm⁻¹ are associated with stretching vibrations of C-H groups. The symmetrical and asymmetrical C-H in-plane bending vibrations of CH₃ groups can be expected in the region 1300-1500 cm⁻¹, as well as, the bands corresponding to N-H in-plane and C-N bond stretching vibration, which is overlapped with C-H vibration. The broad peak between 3300- 3600 cm⁻¹ was due to the NH₂ stretch of the amine group overlapped with OH stretching vibration [7].

Adsorption was performed from the solution which contained 10 mg As dm⁻³. It is evident that ClinH⁺-APTES was more efficient adsorbent for As(III) ions than MOR-APTES (Fig. 5a). The modified natural zeolite ClinH⁺-APTES adsorbed 2.5, while the synthetic zeolite prepared in the same way, bound 1.9 mg As/g zeolite.

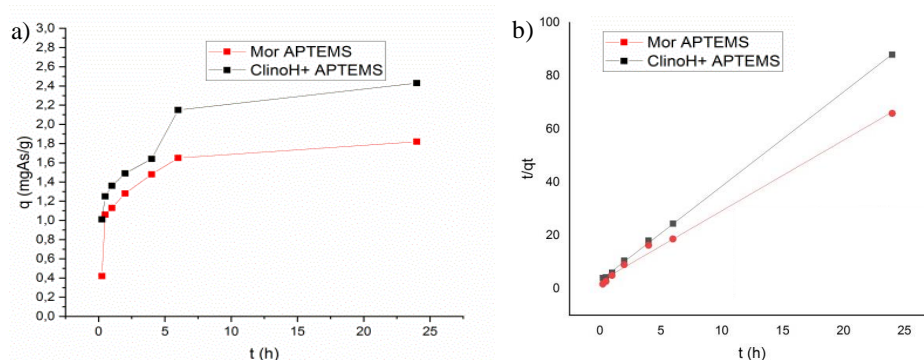


Figure 5. a) As concentration in mg/g on ClinH⁺-APTES and MOR-APTES; b) Lagergren pseudo-second-order kinetic model applied to the adsorption data for ClinH⁺-APTES and MOR-APTES.

Different kinetic models were used to describe the obtained experimental data. The correlation factors value (R^2) for both samples of 0.99 confirmed that adsorption kinetics follows the Lagergren pseudo-second order model (Fig. 5b).

CONCLUSION

The modification of natural and synthetic zeolite by (3-aminopropyl)triethoxysilane presents a new approach to the synthesis of efficient adsorbents for arsenic removal from aqueous solutions. This could contribute to resolving the real issues of wastewater treatment from different industries. The adsorbent containing low-cost natural zeolite-clinoptilolite showed a better affinity for As(III) adsorption than synthetic mordenite. The kinetic data follows the Lagergren pseudo-second-order model.

REFERENCES

- [1] R. Soni and D.P. Shukla, *Chemosphere*, 2019, **219**, 504-509.
- [2] L.K. Wu, H. Wu, Z.Z. Liu, H.Z. Cao, G.Y. Hou, Y.P. Tang and G.Q. Zheng, *J. Hazard. Mater.*, 2017, **347**, 15-24.
- [3] N. Rajić, Dj. Stojaković, S. Jevtić, N. Zabukovec Logar, J. Kovač, and V. Kaučič, *J. Hazard. Mater.*, 2009, **172**, 1450-1457.
- [4] N. Rajić, Dj. Stojaković, M. Jovanović, N. Zabukovec Logar, M. Mazaj and V. Kaučič, *Appl. Surf. Sci.*, 2010, **257**, 1524-1532.
- [5] Š. Cerjan-Stefanović, N. Zabukovec Logar, K. Margeta, N. Novak Tušar, I. Arčon, K. Maver, J. Kovač and V. Kaučič, *Micropor. Mesopor. Mater.*, 2007, **105**, 251-259.
- [6] Y. Garcia-Basabe, I. Rodriguez-Iznaga, L. C. De Menorval, P. Llewellyn, G. Maurin, D. W. Lewis, R. Binions, M. Autie, and A. R. Ruiz-Salvador, *Micropor. Mesopor. Mater.*, 2010, **135**, 187-196.
- [7] M. Bayat, V. Javanbakht and J. Esmaili, *Int. J. Biol. Macromol.*, 2018, **116**, 607-619.